

Layered Compounds

Two-dimensional layers

Graphite and Graphene

Clay Minerals


Layered Double Hydroxides (LDHs)

Layered Zirconium Phosphates and Phosphonates


Layered Metal Oxides

Layered Metal Chalcogenides - TiS_2 , MPS_3 (M = V, Mn, Fe, Co, Ni, Zn)

Alkali Silicates and Crystalline Silicic Acids

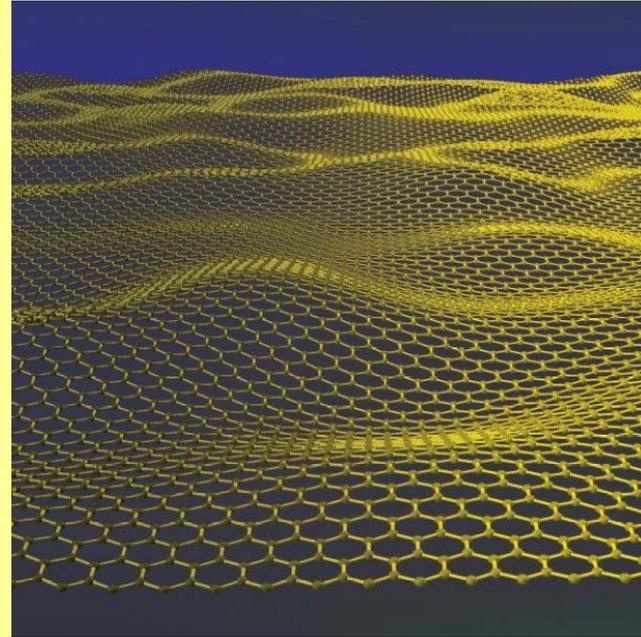


Layered Compounds

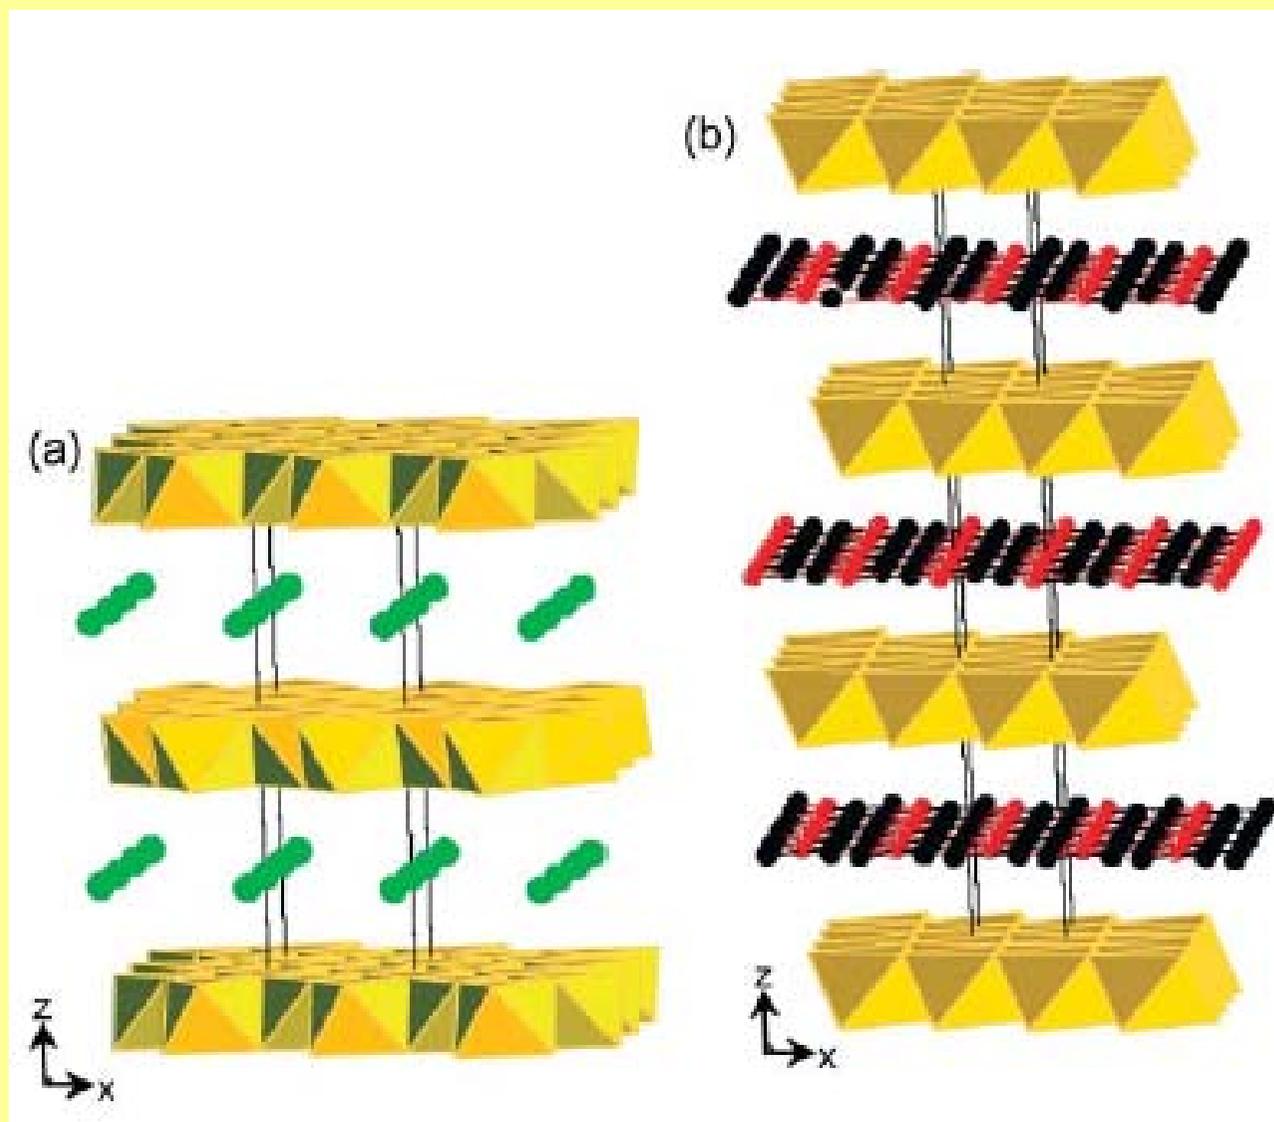


Host-Guest Structures

Host dimensionality


3D

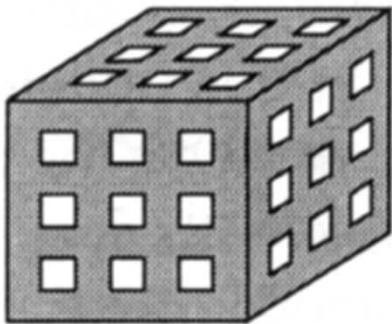


2D

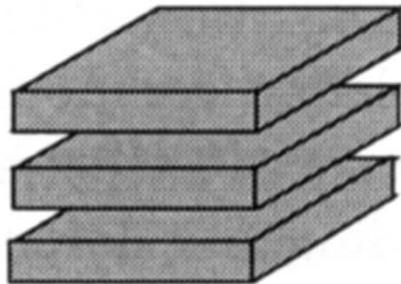

1D

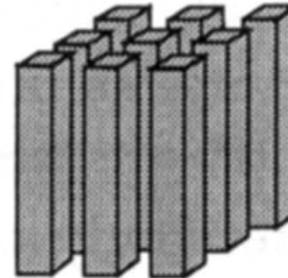

0D

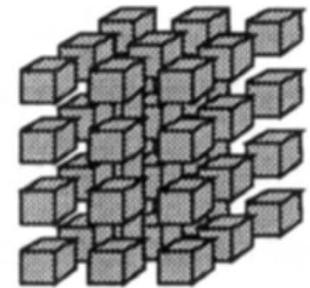


TOPOTACTIC SOLID-STATE REACTIONS = modifying existing solid state structures while maintaining the integrity of the overall structure


Intercalation

Intercalation


Insertion of molecules between layers

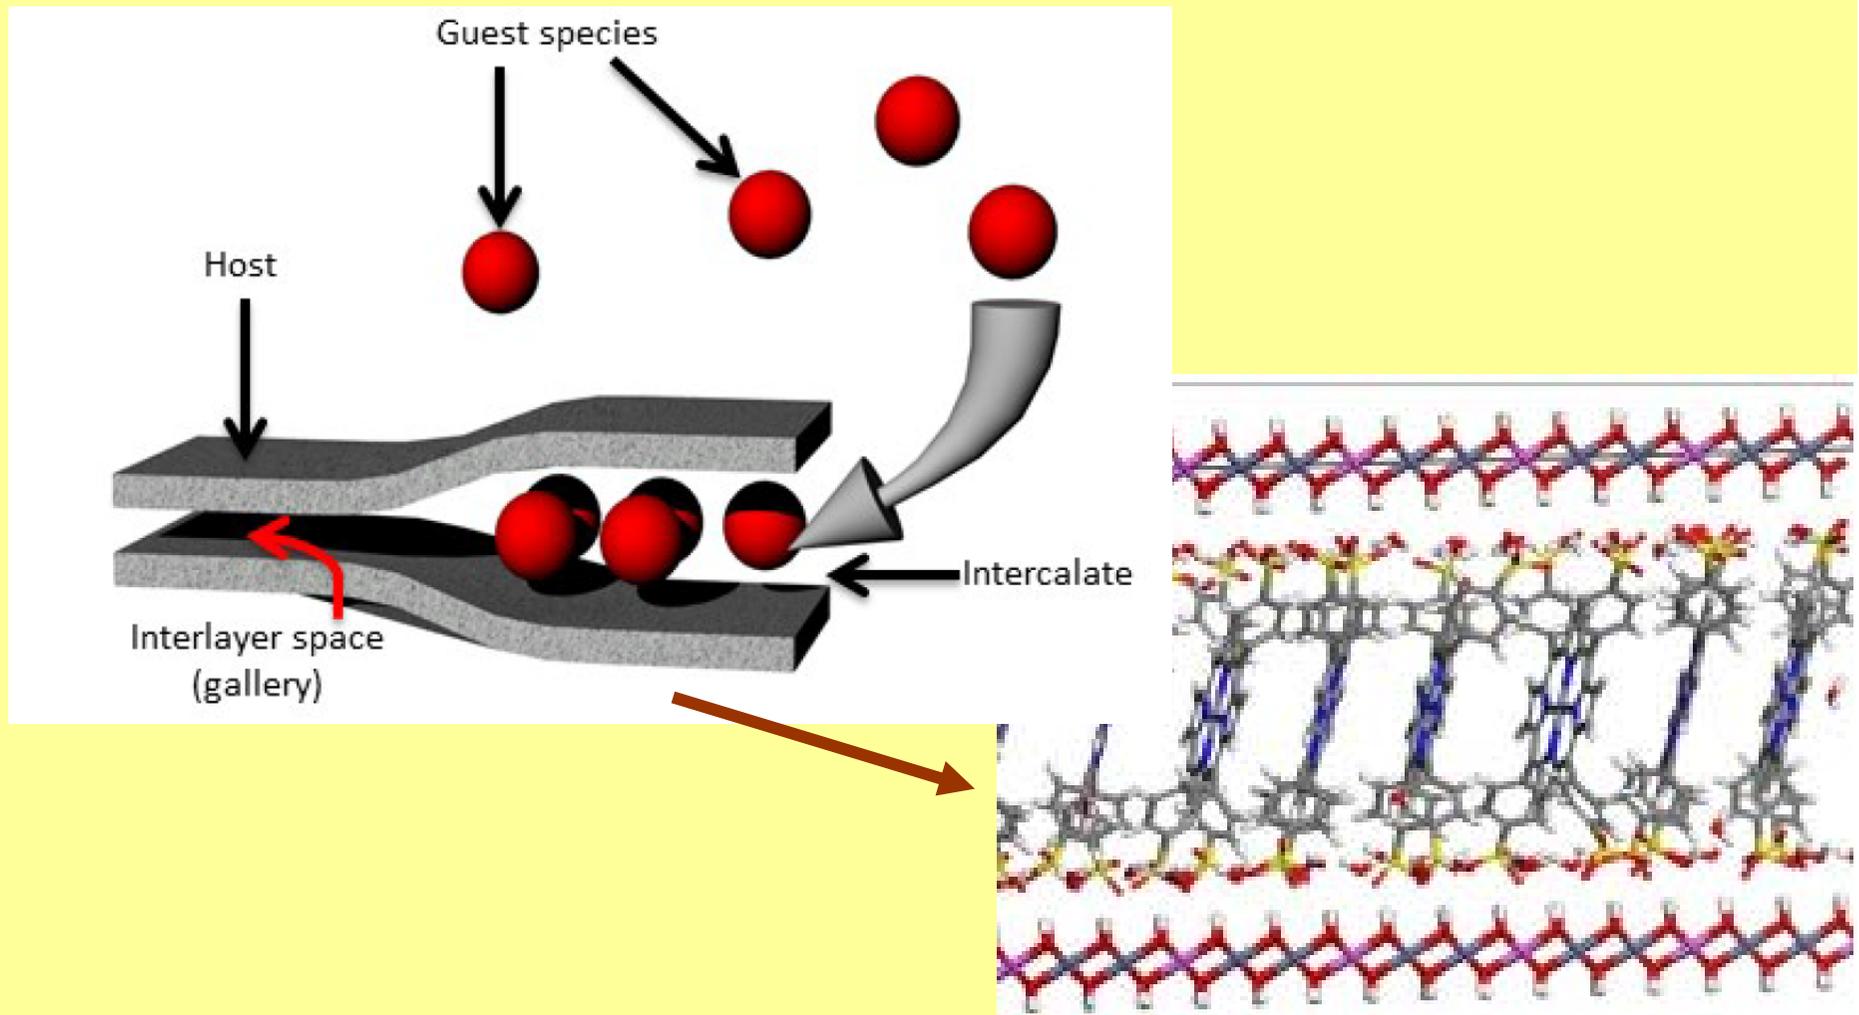


Intercalation

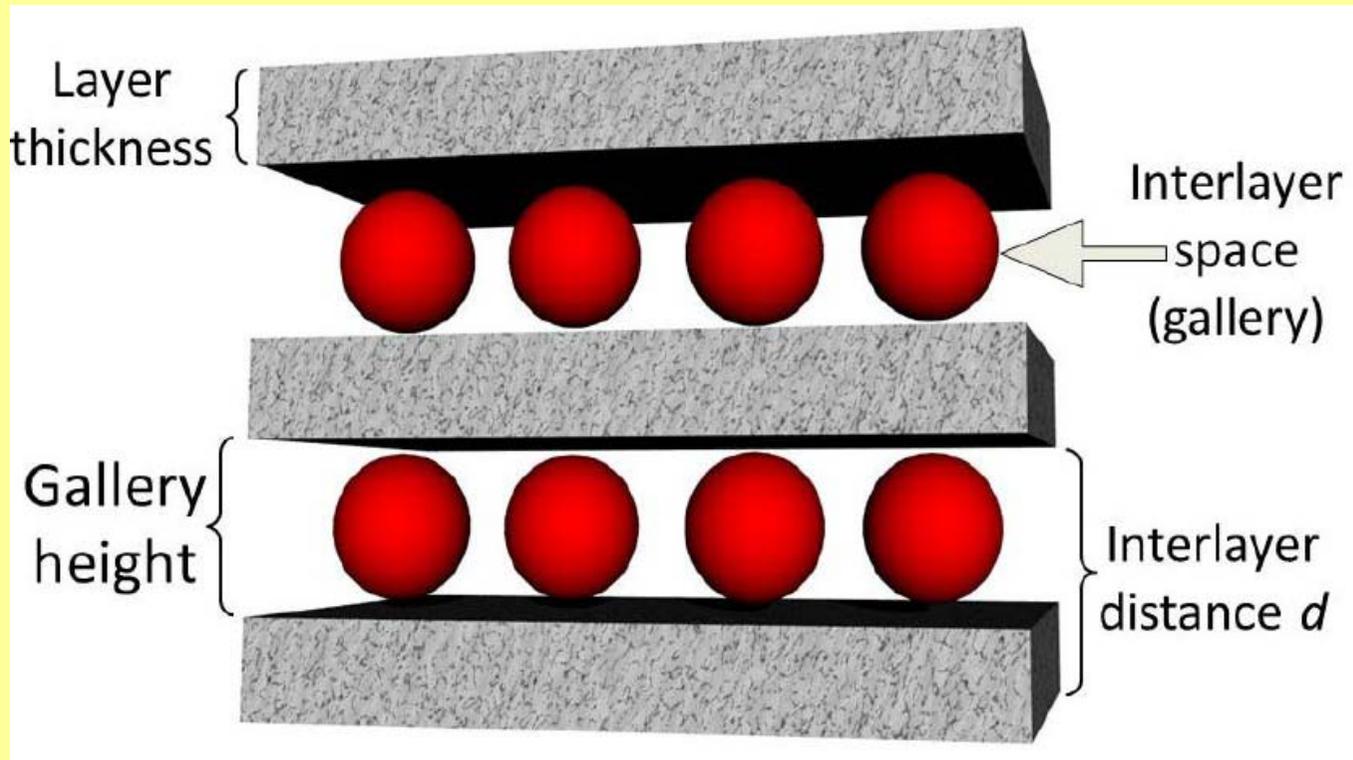


Intercalation

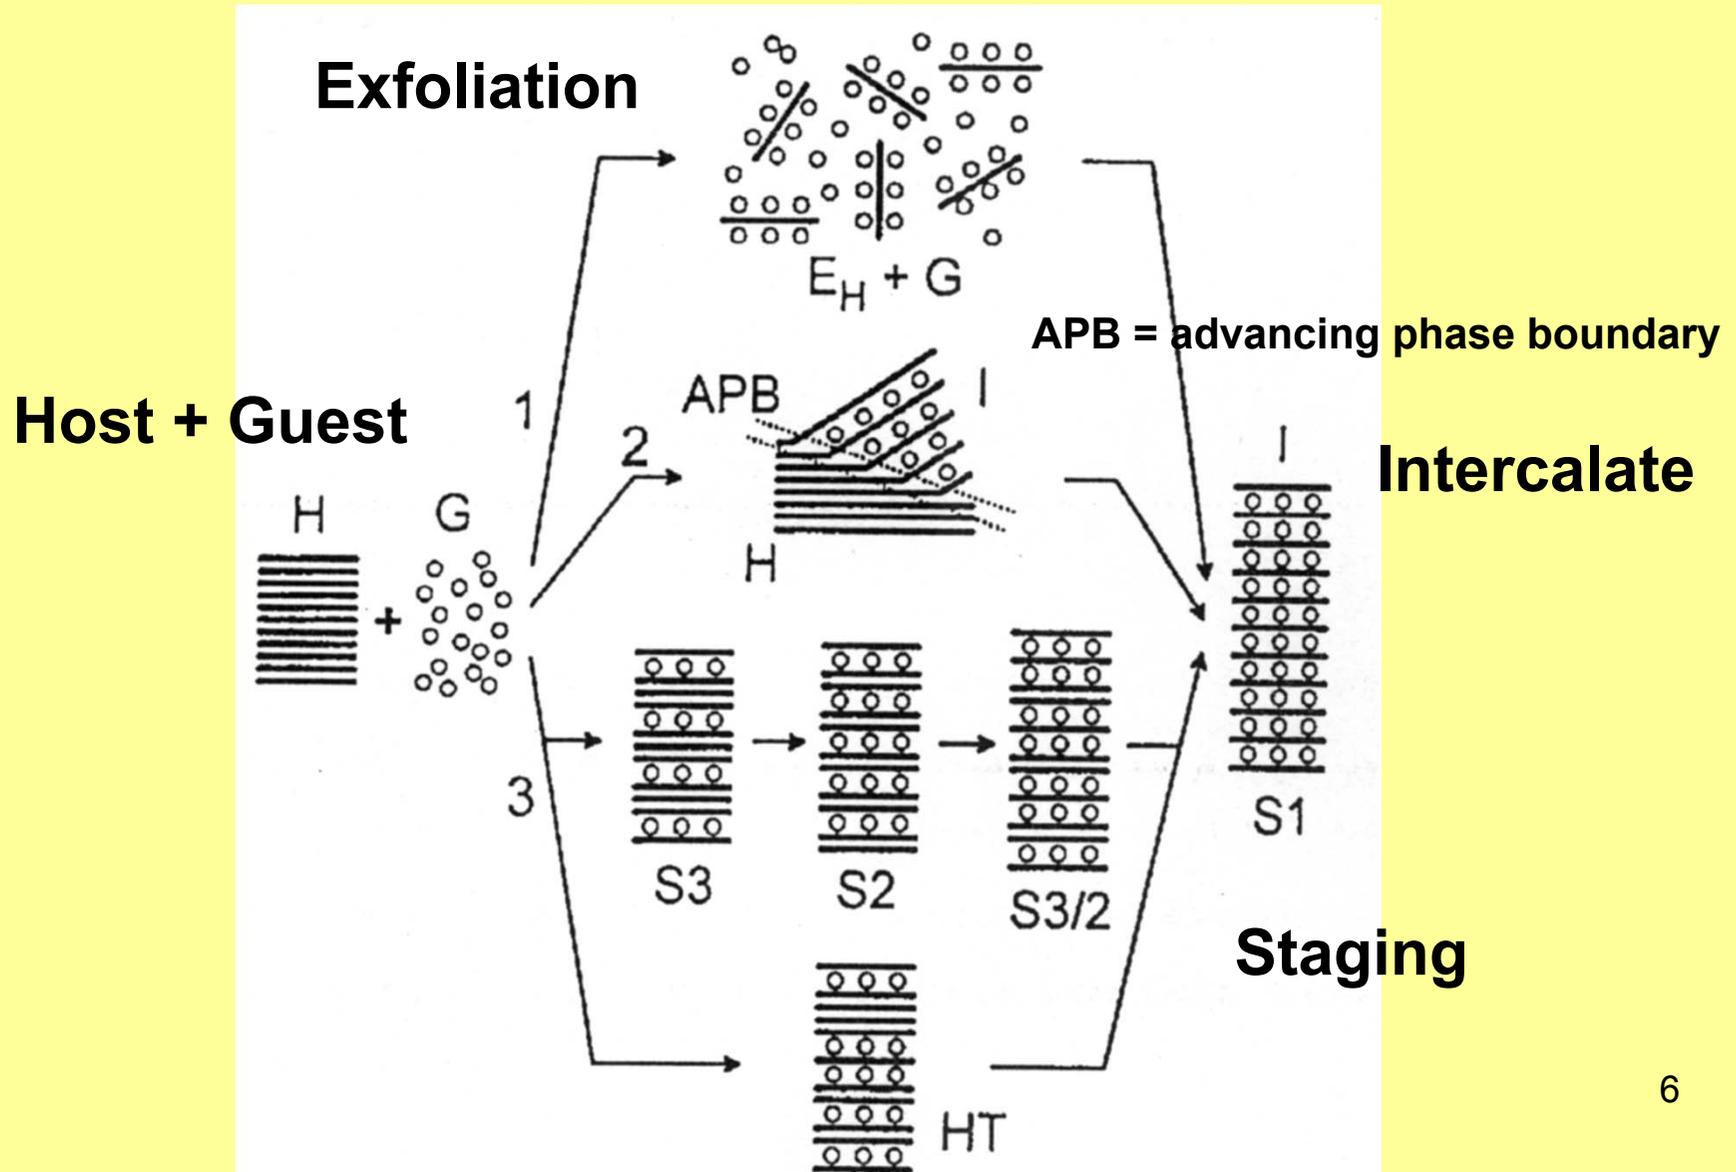

Exfoliation

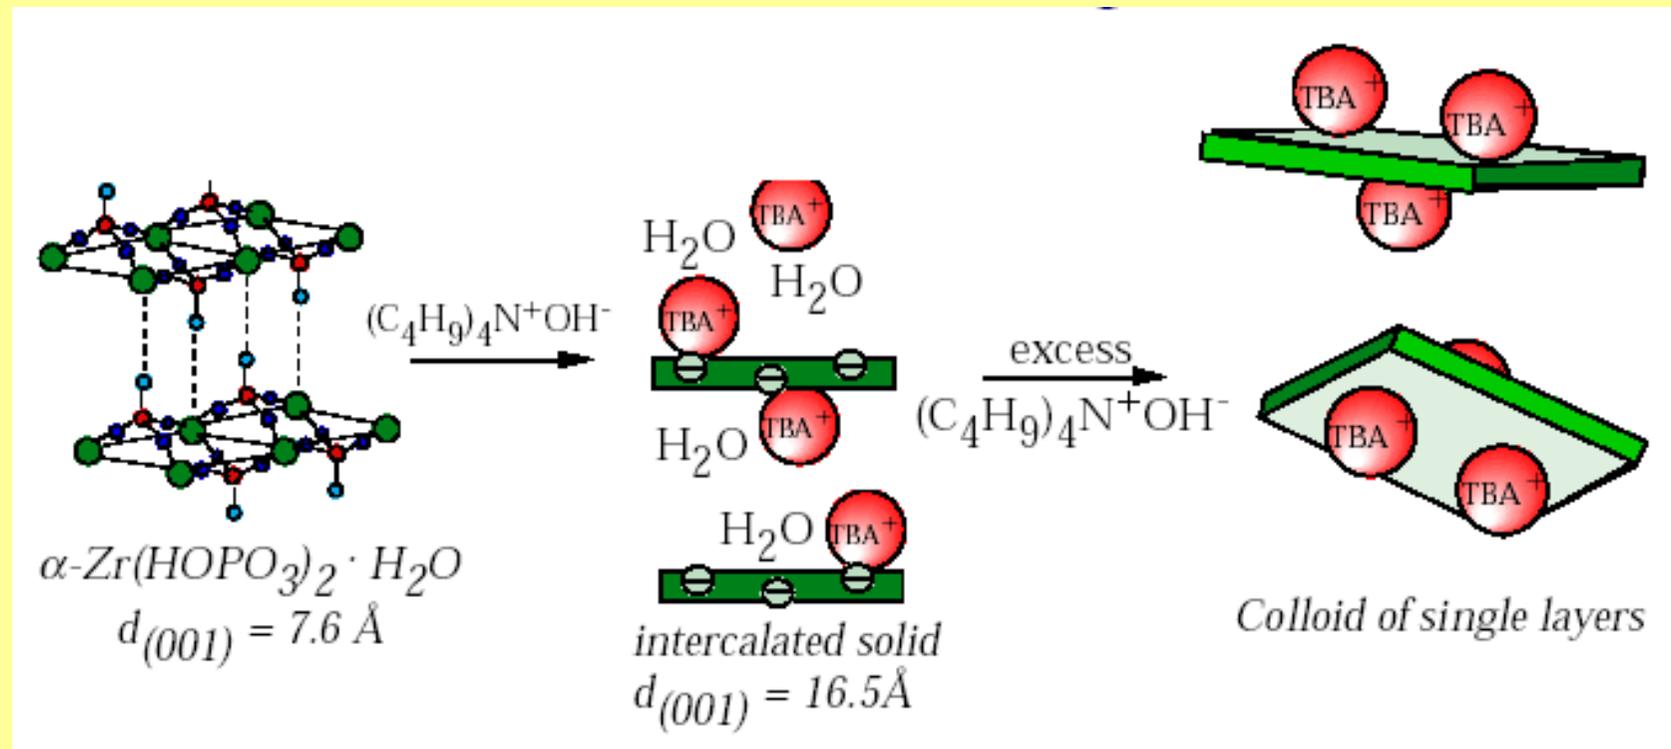


APB = advancing phase boundary



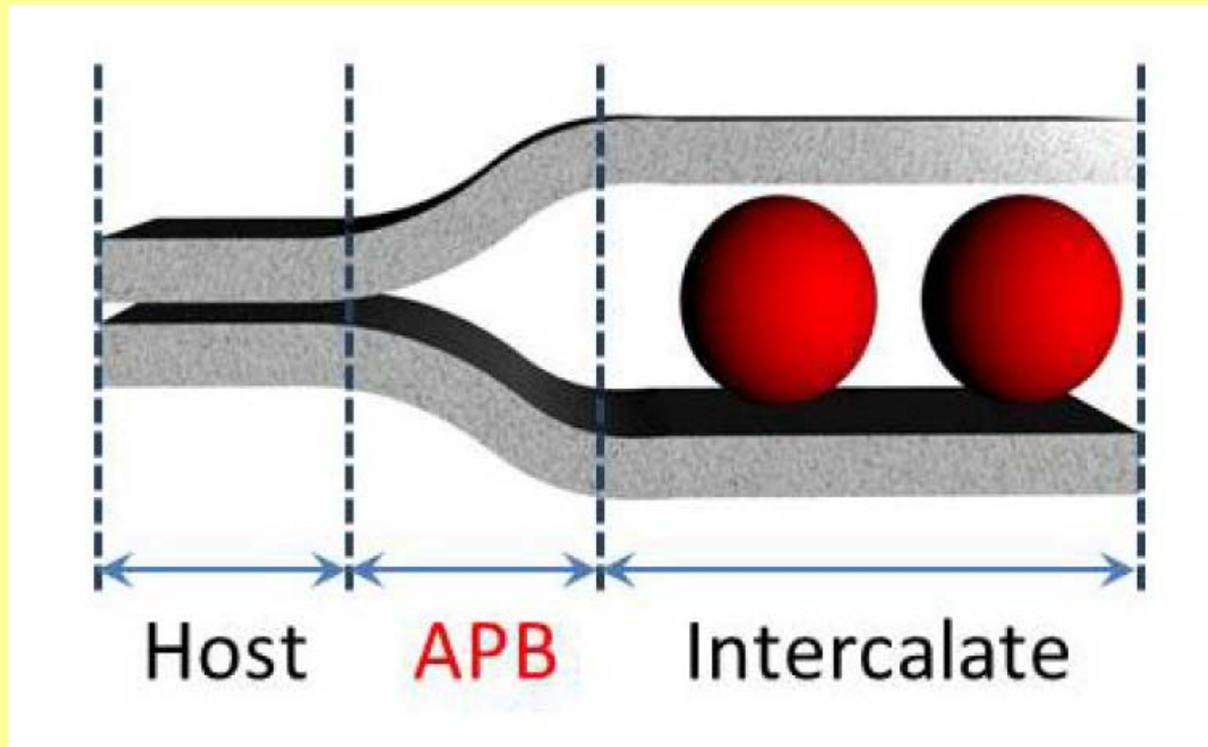


APB = advancing phase boundary

Staging

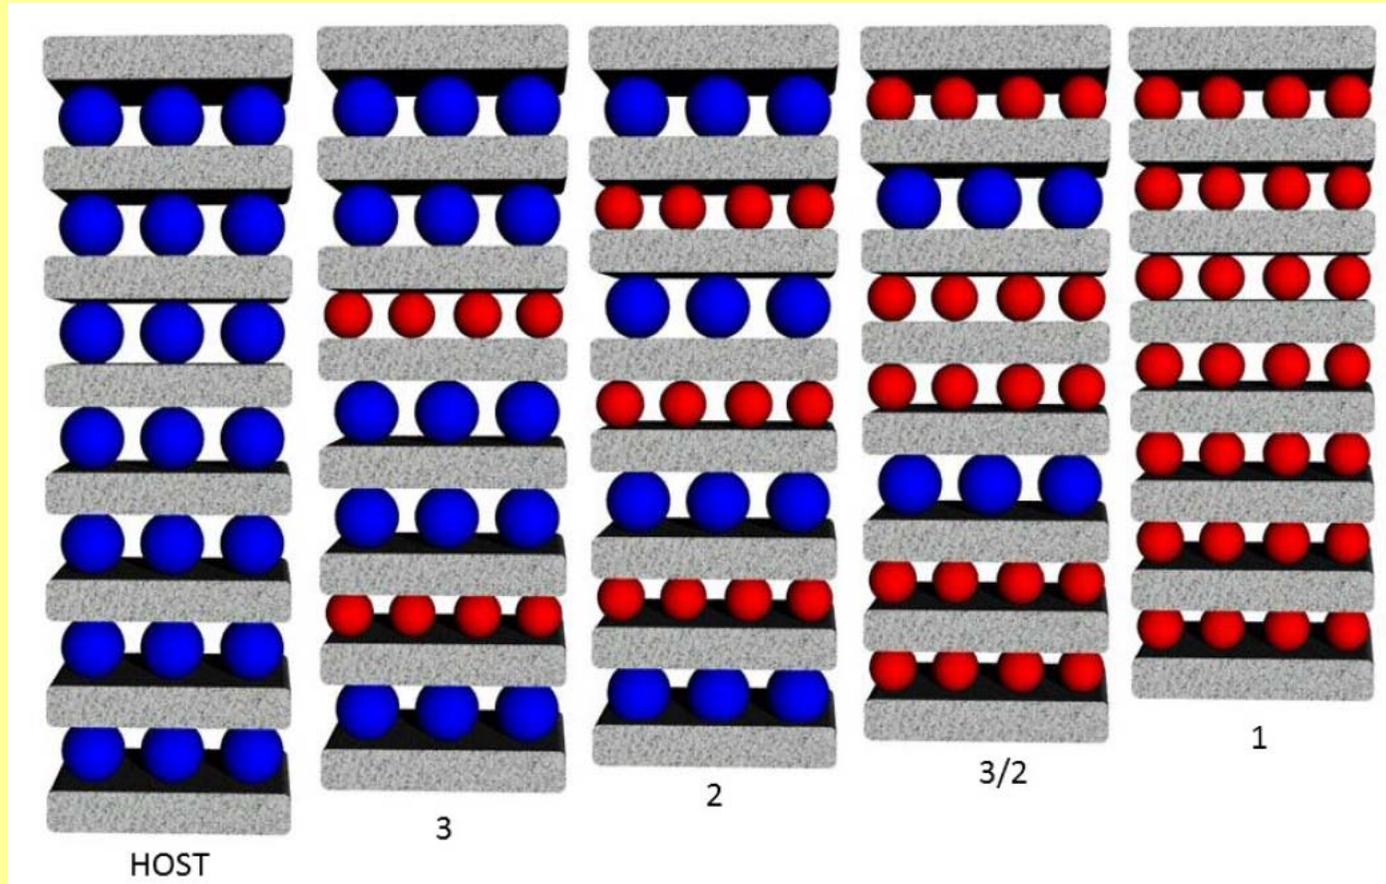


Hendricks-Teller effect

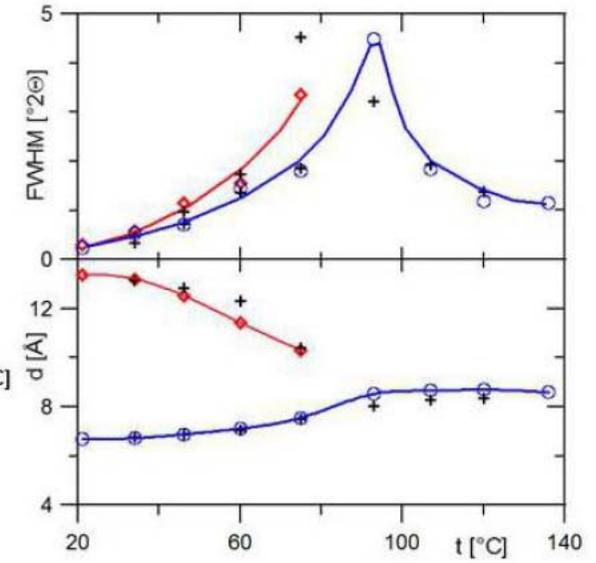
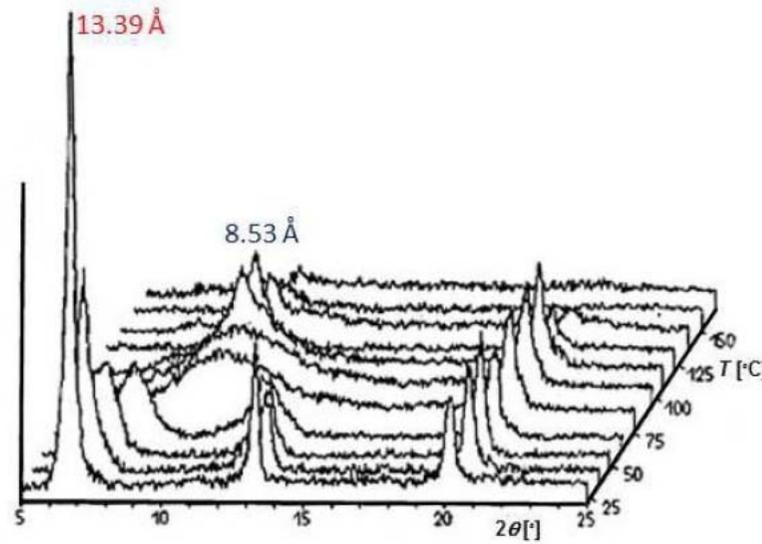
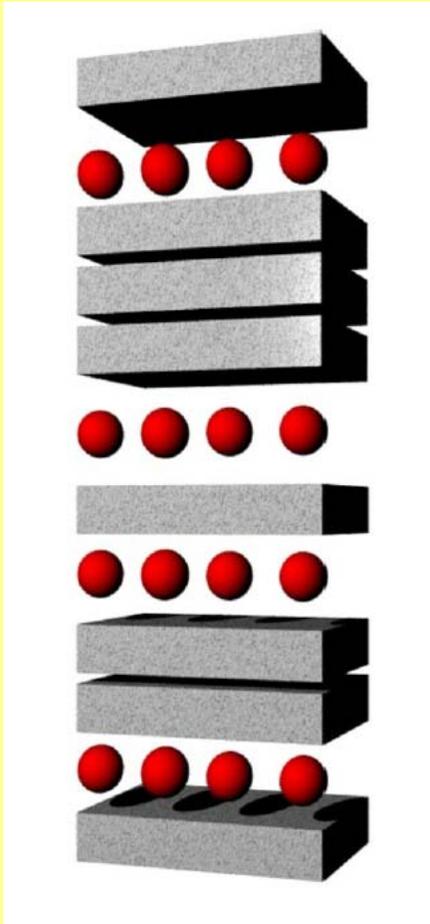


HT = galleries are filled randomly

Intercalation


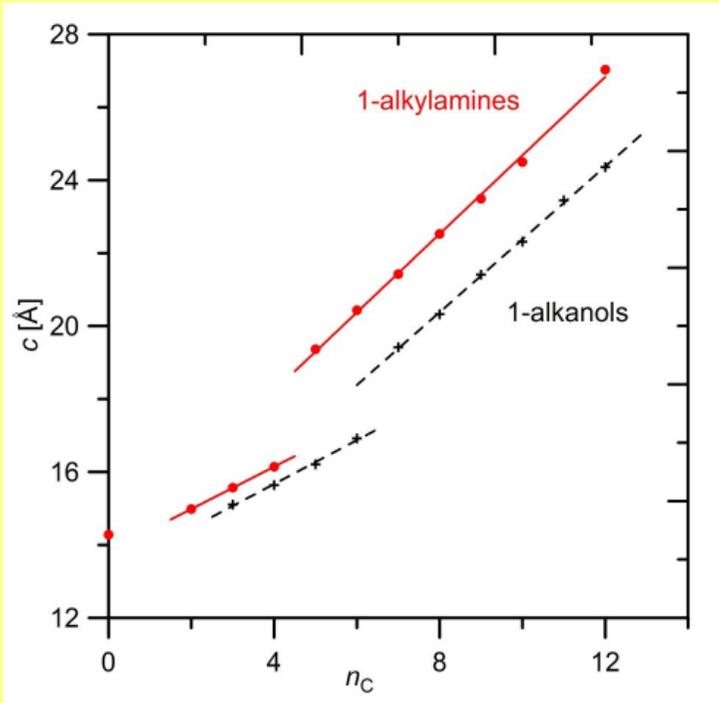


Dependence of the basal spacing of the intercalates of the alkylamines (circles) and alkanols (crosses) on the number of carbon atoms n_C in $\text{SrC}_6\text{H}_5\text{PO}_3 \cdot 2\text{H}_2\text{O}$

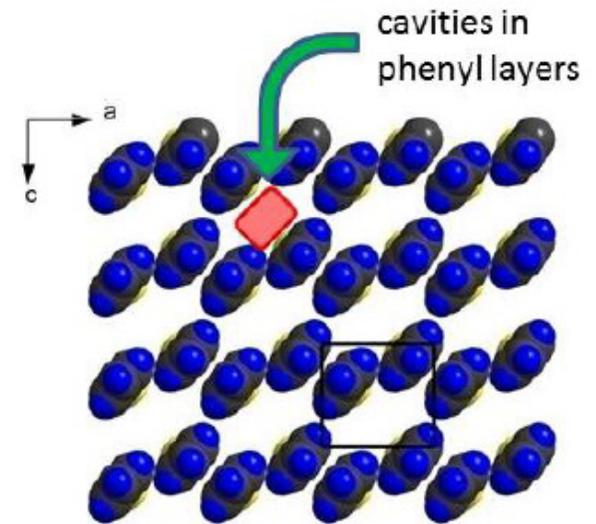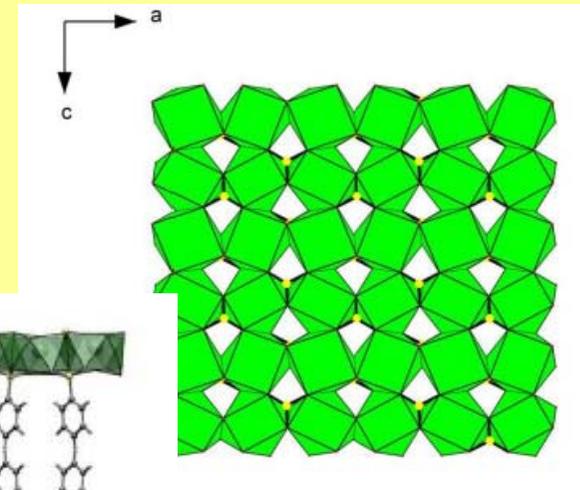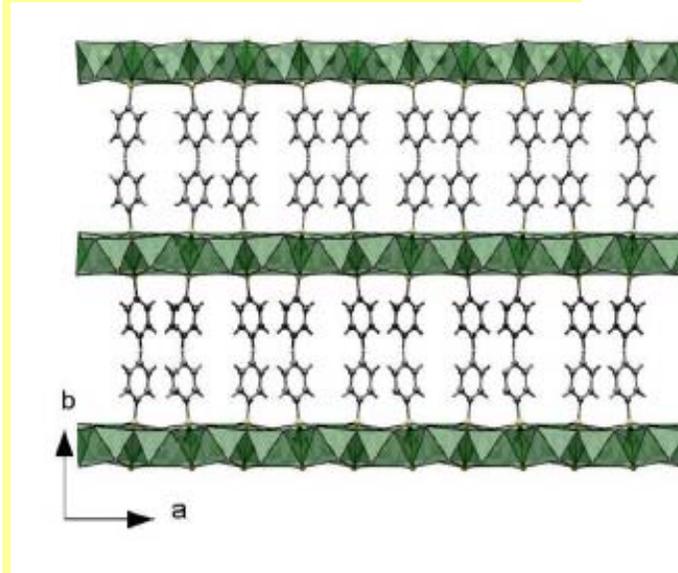

Graphite

ABABAB

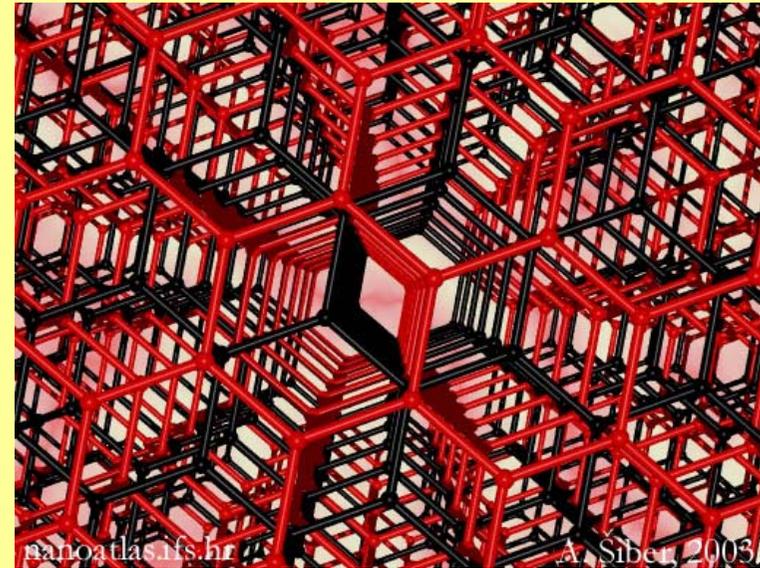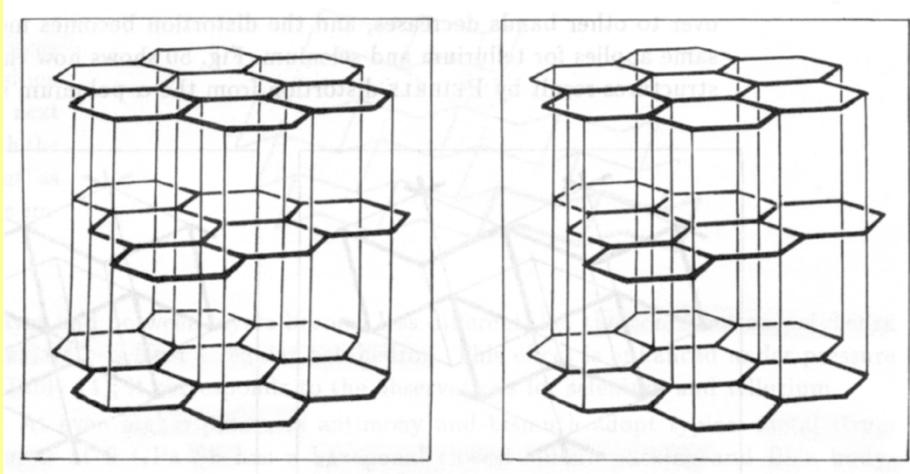

**Graphite sp^2 sigma-bonding in-plane p-p-bonding out of plane
Hexagonal graphite = two-layer ABAB stacking sequence**

**SALCAOs of the p-p-type create the valence and conduction
bands of graphite, very small band gap, metallic conductivity
properties in-plane, 10^4 times that of out-of plane conductivity**

Graphite

GRAPHITE INTERCALATION



C₈K potassium graphite ordered structure

Ordered K guests between the sheets, K to G charge transfer



AAAA stacking sequence


reduction of graphite sheets, electrons enter CB

K nesting between parallel eclipsed hexagonal planar carbon six-rings



Graphite

Intercalates

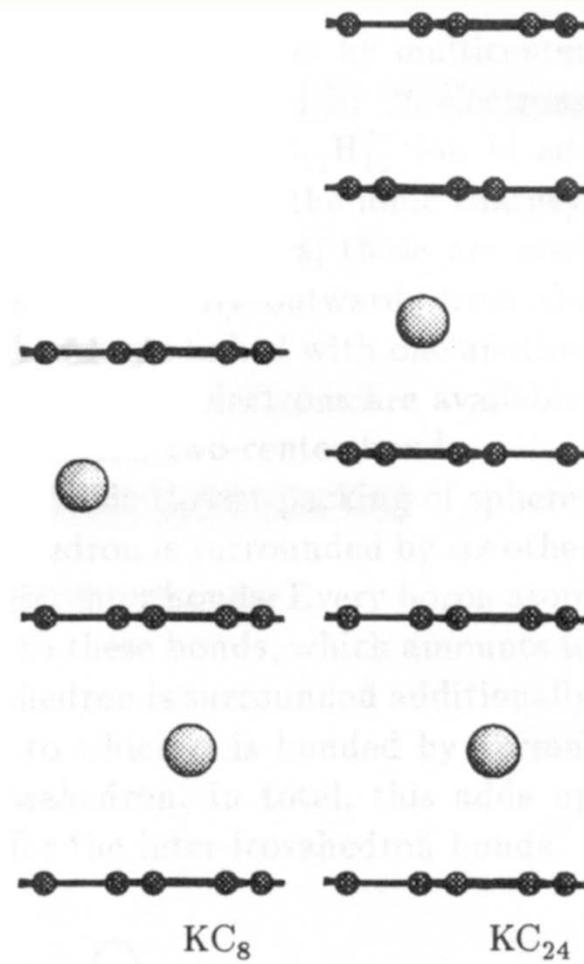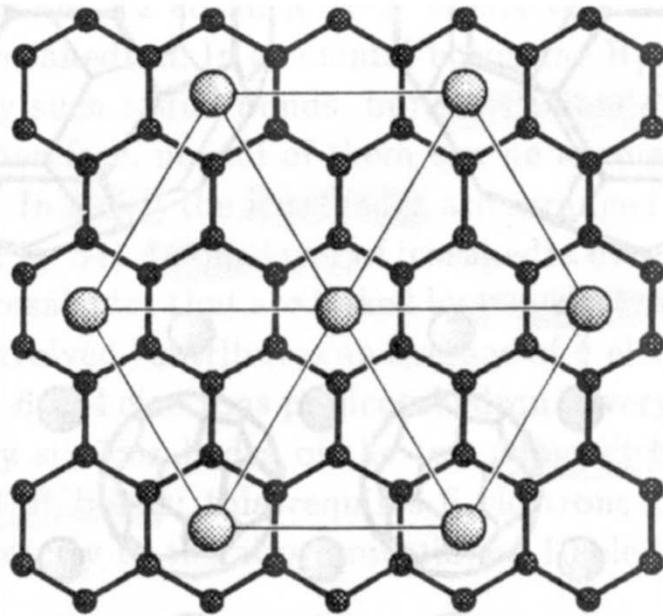


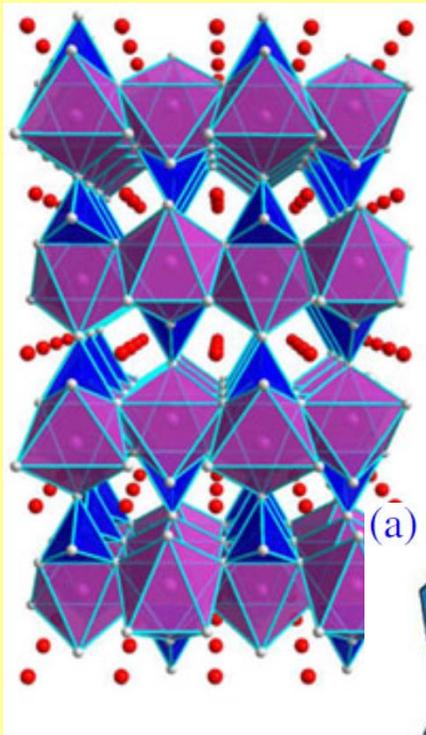

(a)

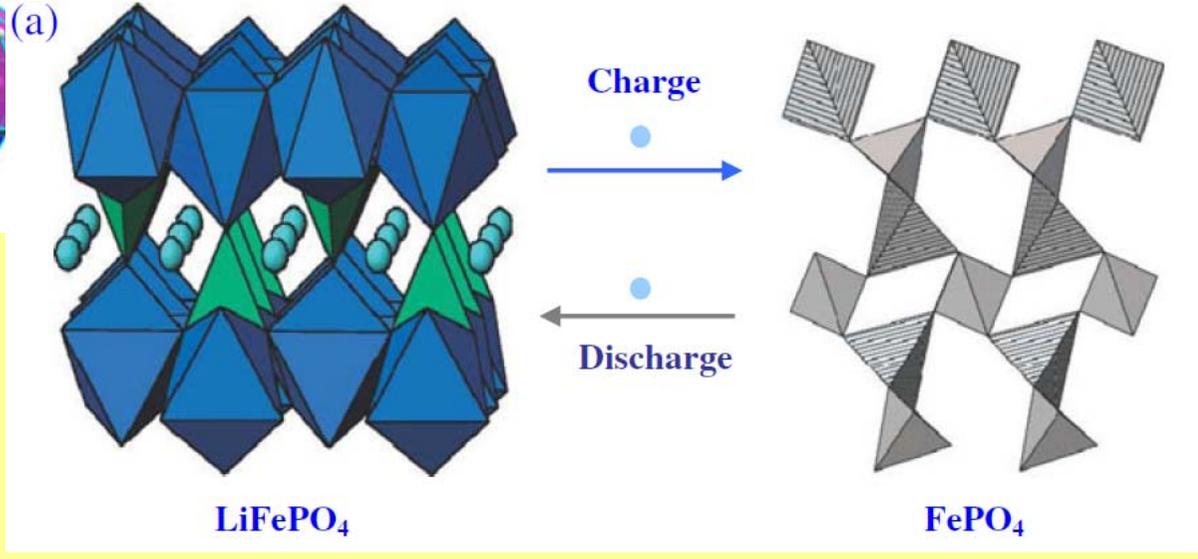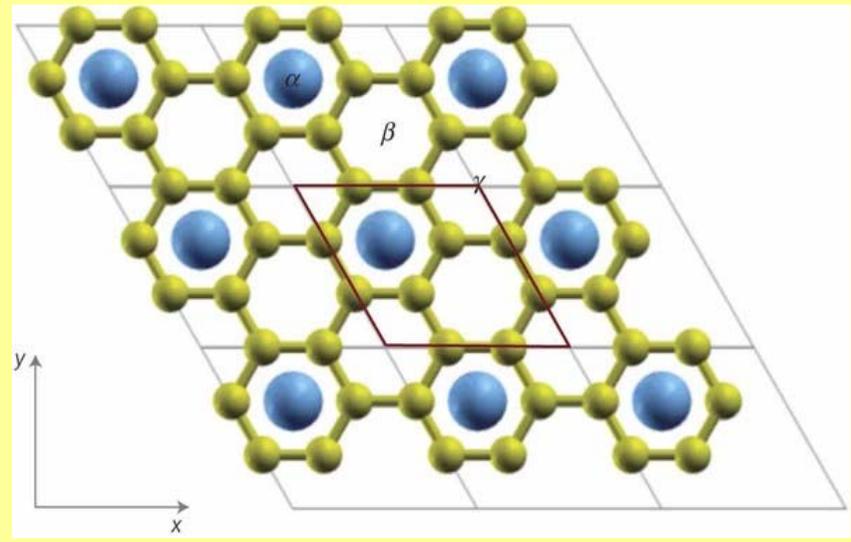

Li-ion Cells

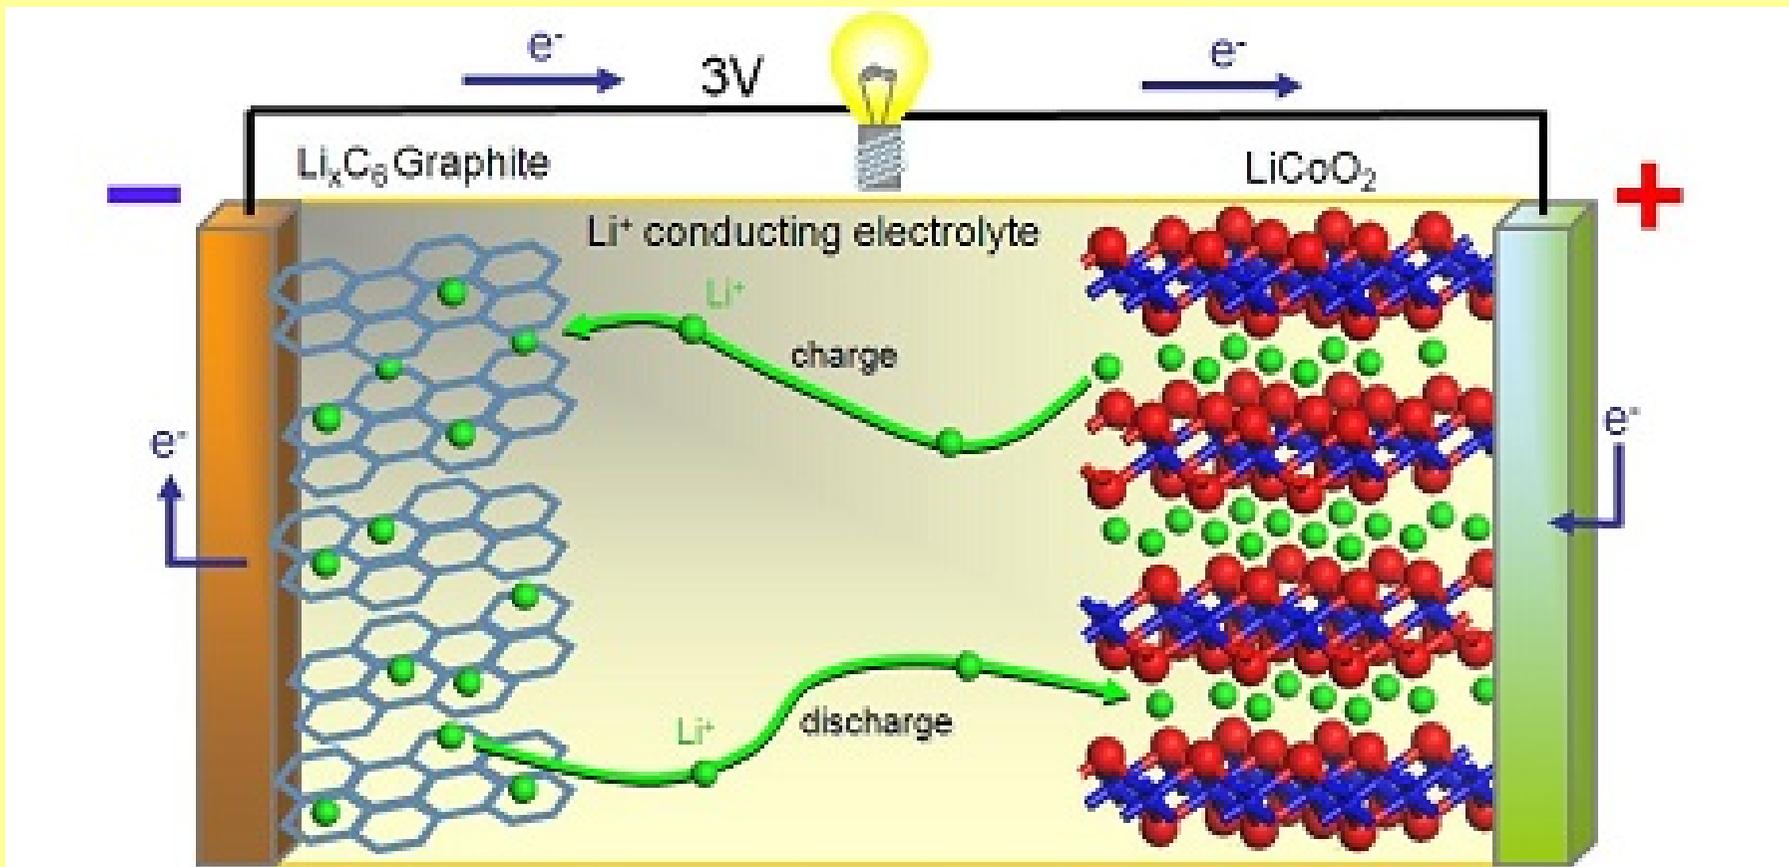

Graphene

- **Discovery – 2004**
- **Exotic properties:**
 - Firm structure
 - Inert material
 - Hydrofobic character
 - Electric and thermal conductivity
 - High mobility of electrons
 - Specific surface area
(theoretically):
 $2630 \text{ m}^2\text{g}^{-1}$



K. Novoselov




A. Geim





Synthesis of graphene

- **Top down**
 - Mechanical exfoliation
 - Chemical exfoliation
- **Bottom up**
 - CVD, epitaxial growth, ...
- **Defects**
- **Application: diodes, sensors, solar cell, energy storage, composites, ...**

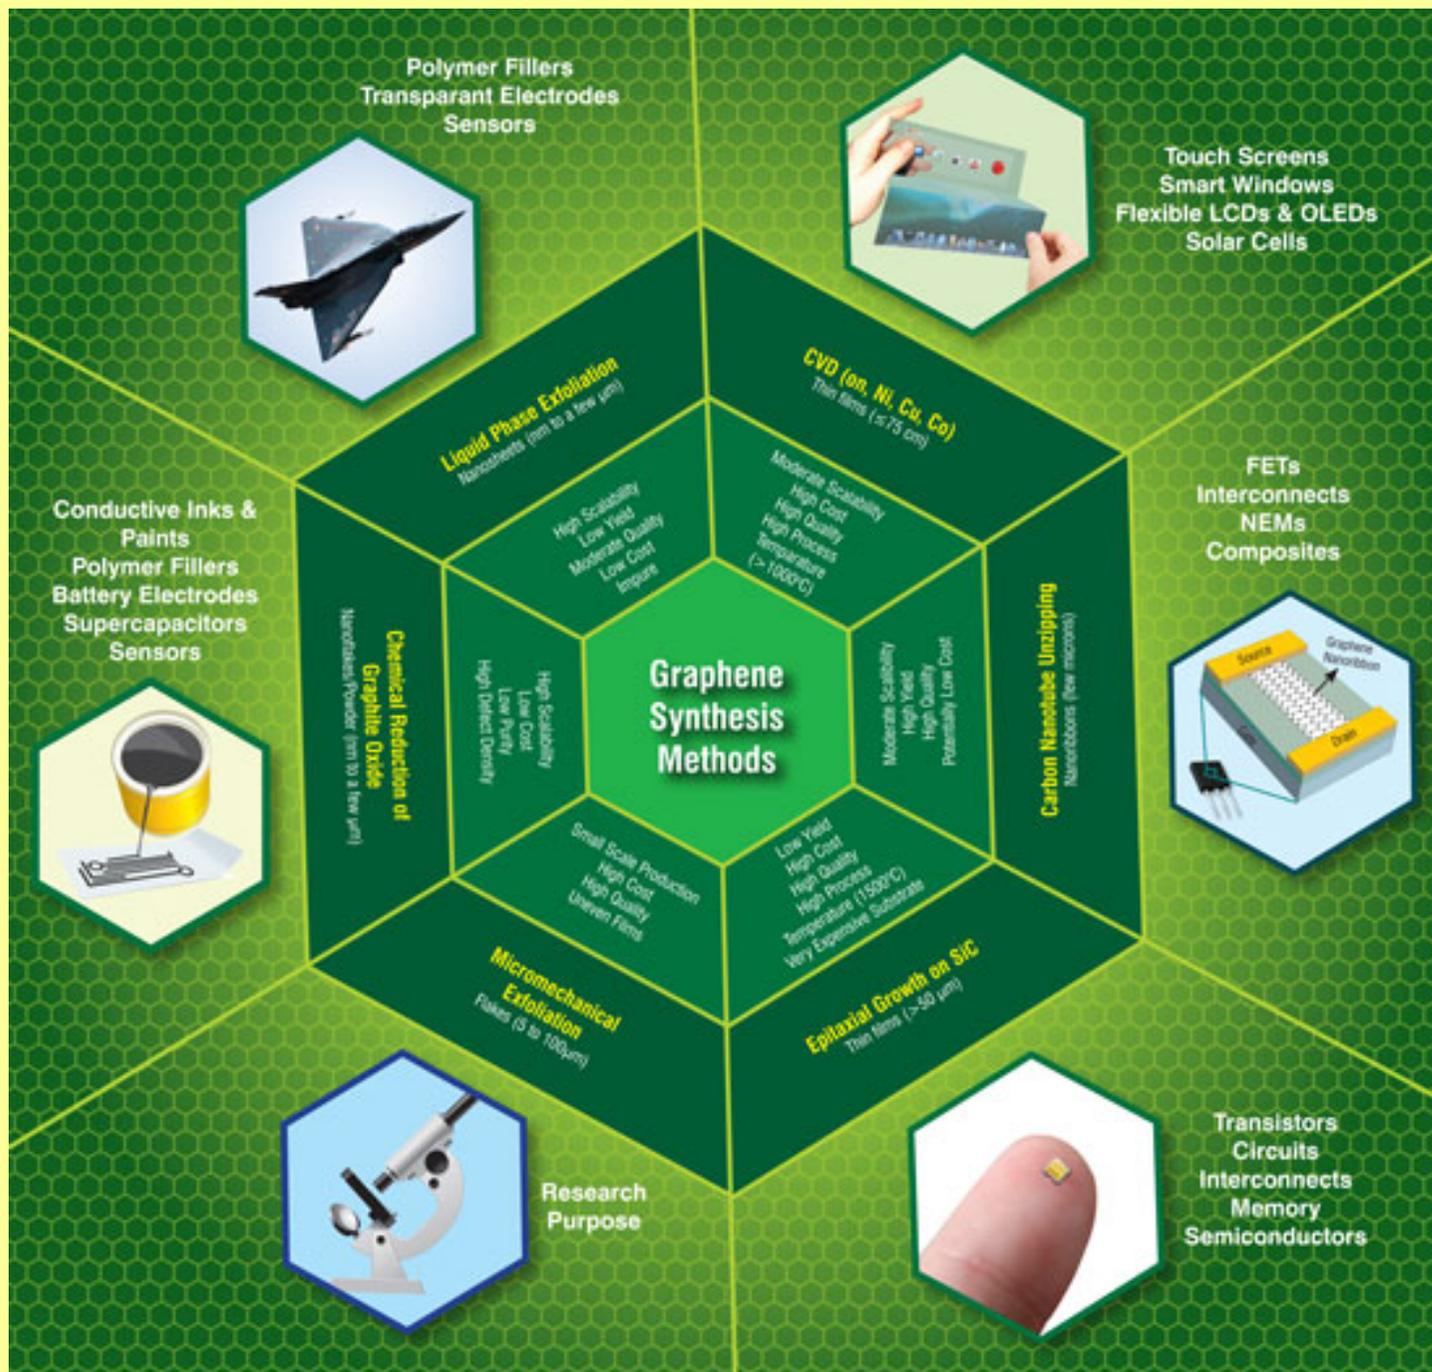

Graphene

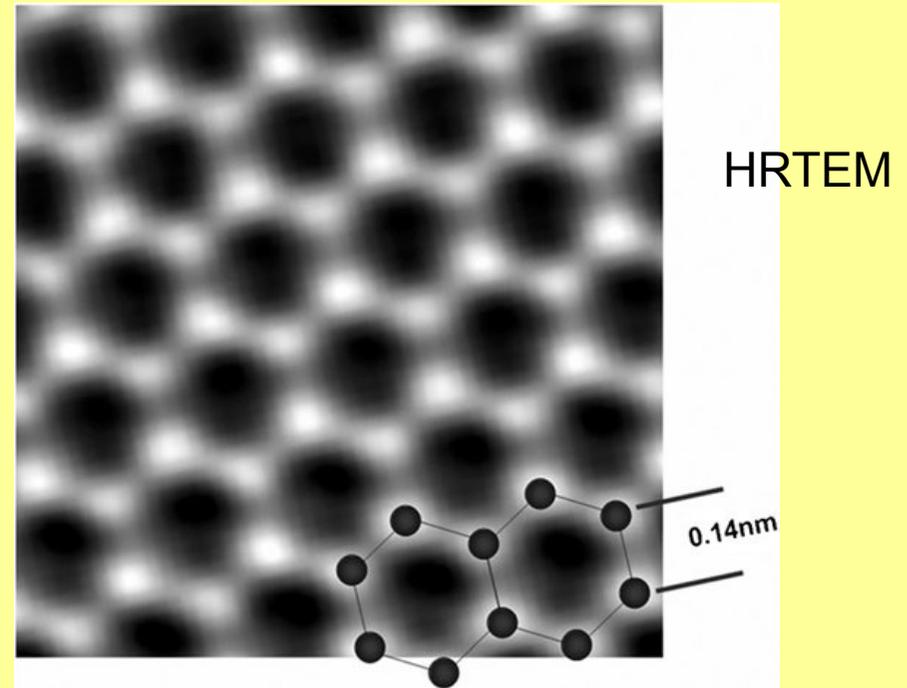
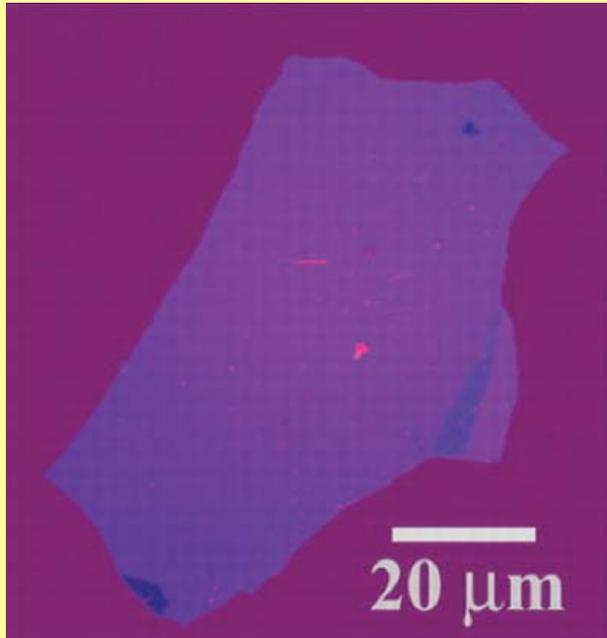


High electric conductivity (metallic)

Optically transparent – 1 layer absorbs 2.3% of photons

High mechanical strength

Graphene

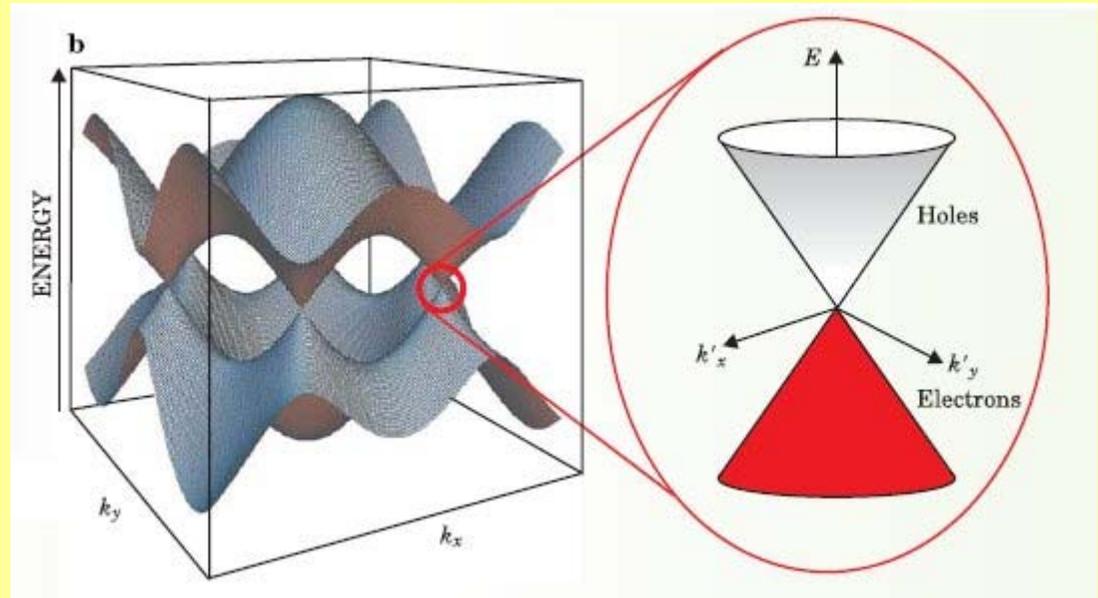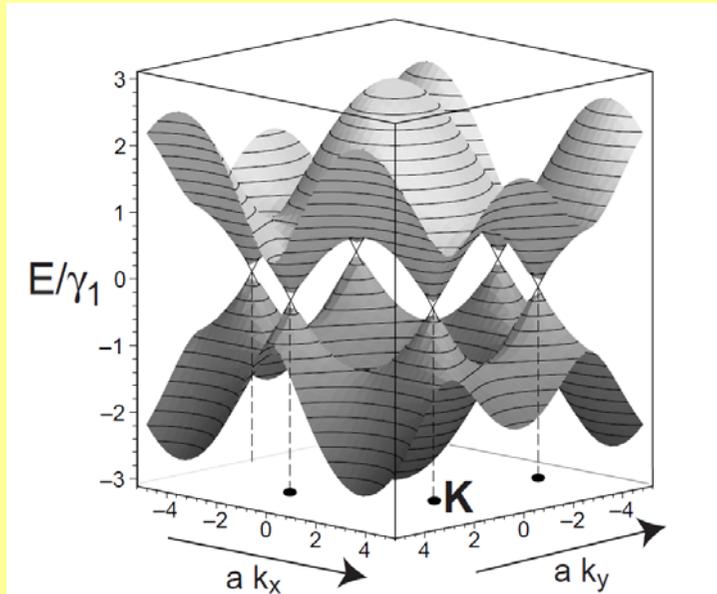


LCAO-band structure of graphene

Graphene


Preparation:


- Scotch tape – layer peeling, flaking
- SiC pyrolysis – epitaxial graphene layer on a SiC crystal
- Exfoliation of graphite (chemical, sonochemical)
- CVD from CH_4 , CH_2CH_2 , or CH_3CH_3 on Ni (111), Cu, Pt surfaces

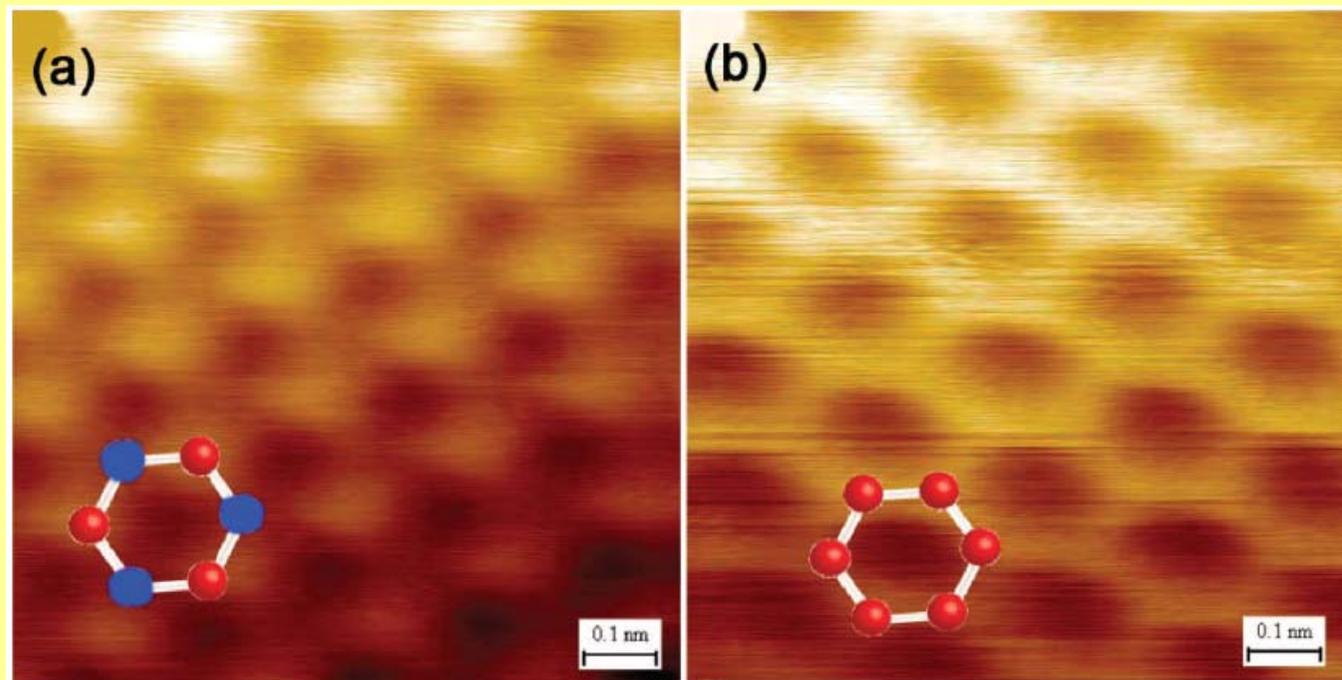

Scotch tape – Layer peeling



Mechanical exfoliation

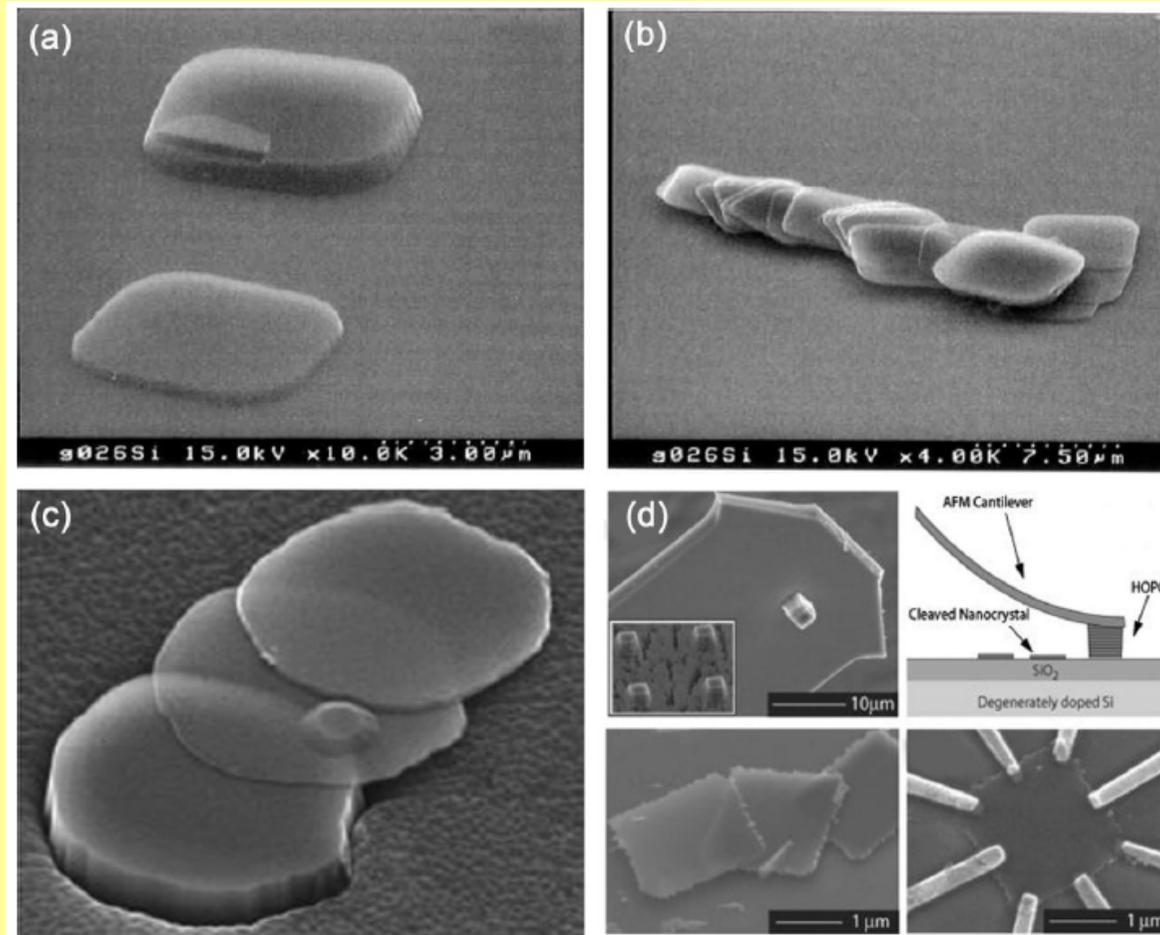


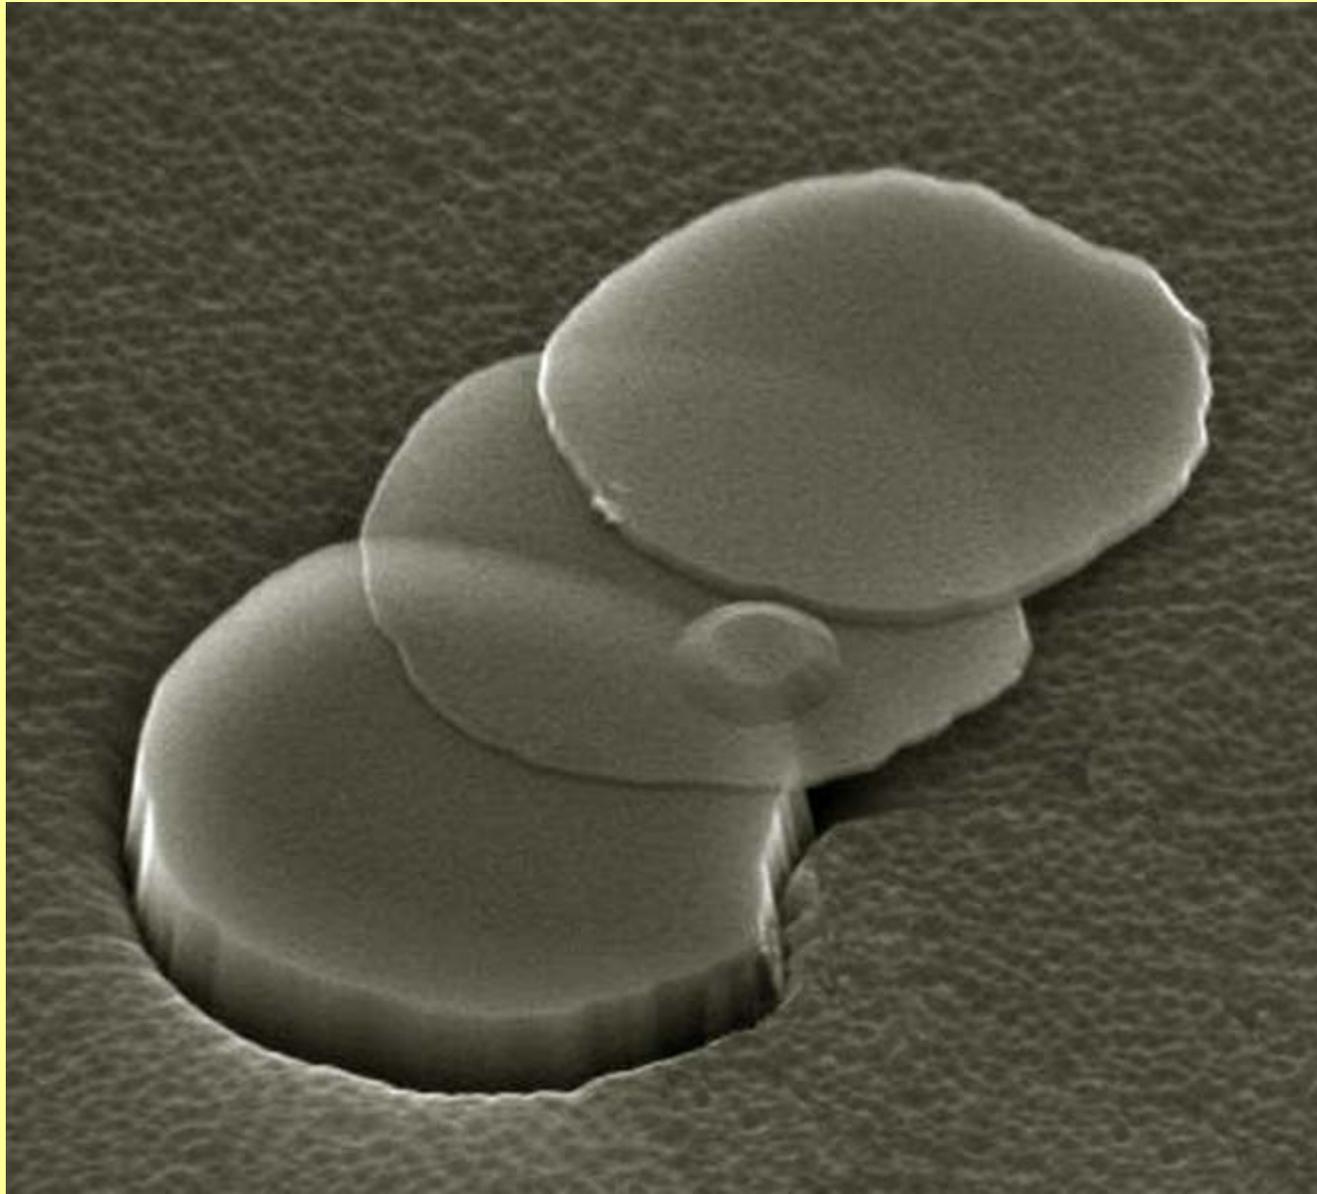

SiC pyrolysis

- Annealing of the SiC crystal in a vacuum furnace (UHV 10^{-10} Torr)
- Sublimation of Si from the surface at 1250 - 1450 °C
- The formation of graphene layers by the remaining carbon atoms

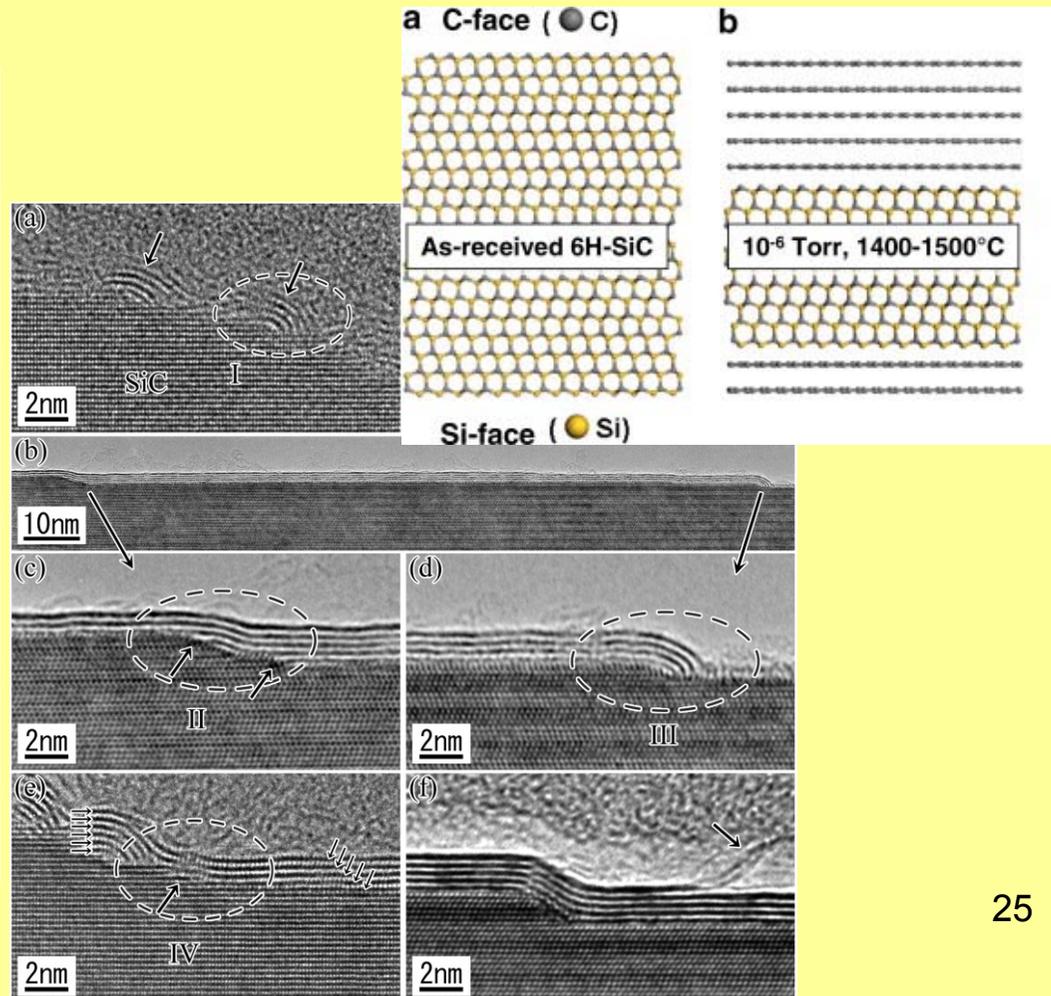
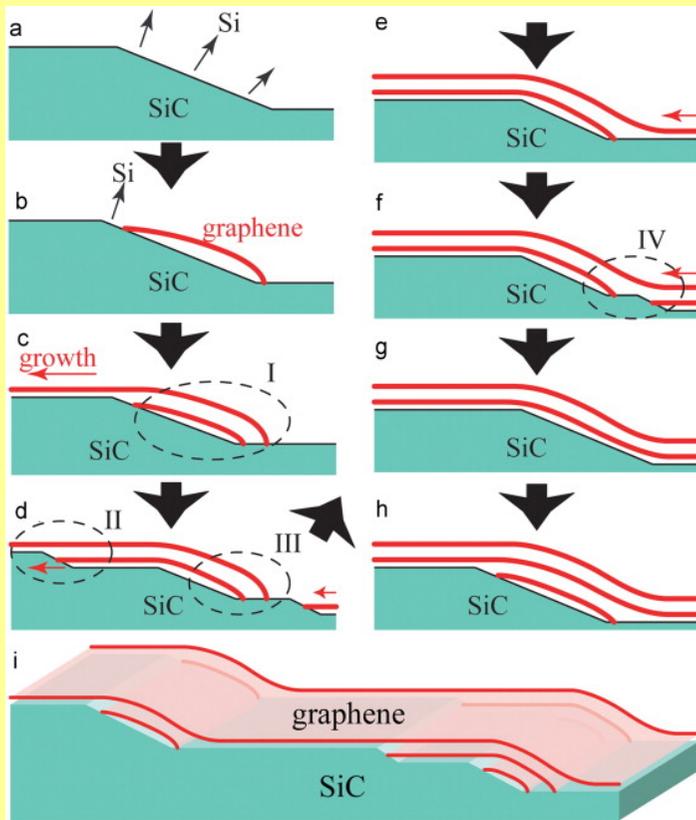


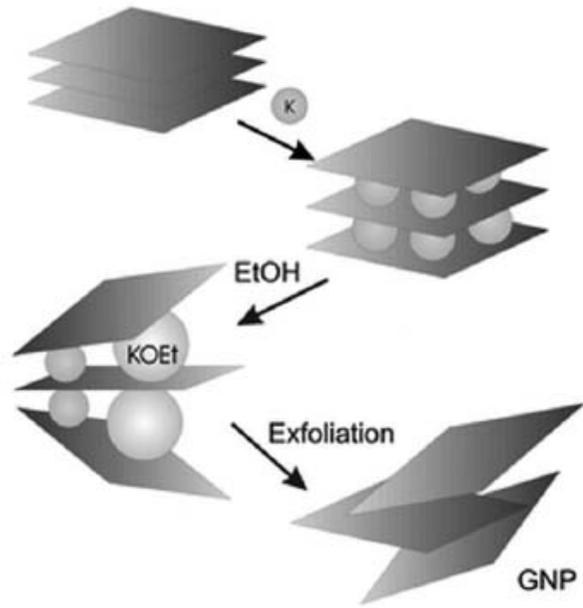




Exfoliation

Chemical exfoliation (surfactant)

Sonochemical exfoliation

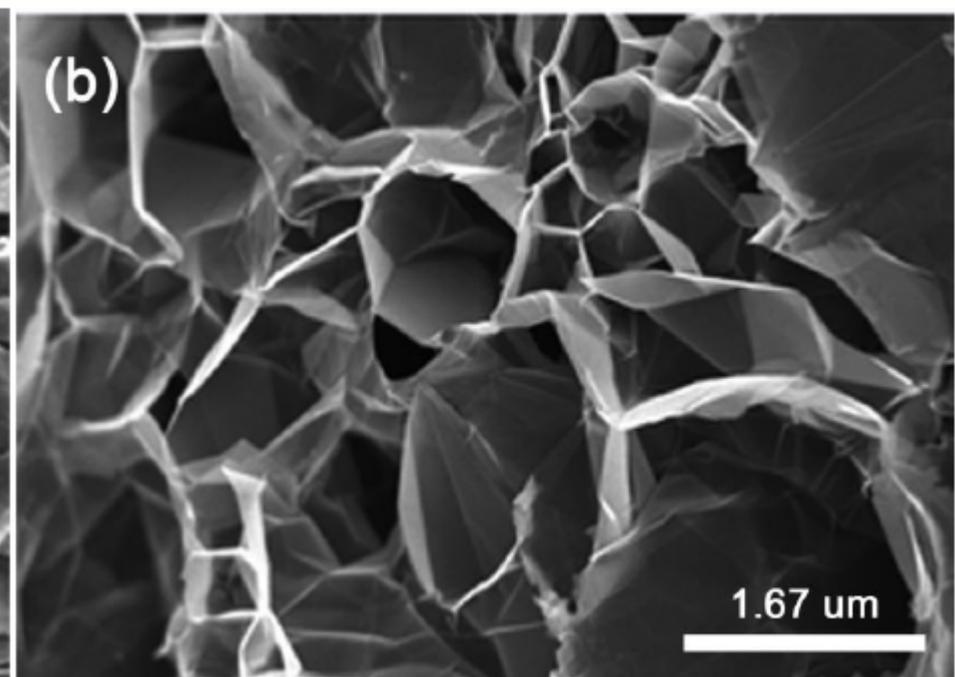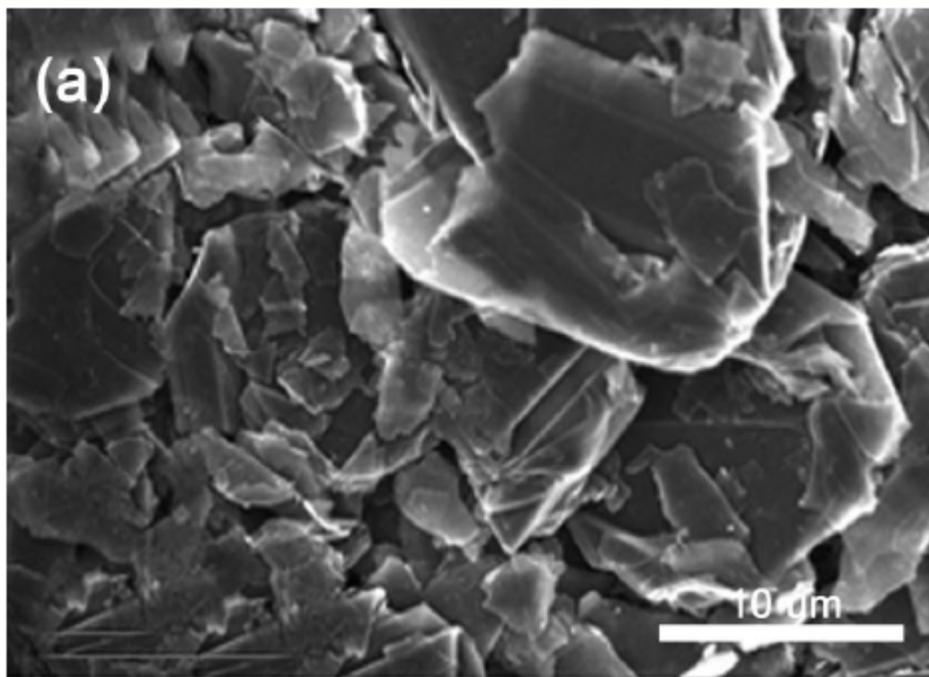

CVD from CH₄ / H₂ on Metal Surfaces

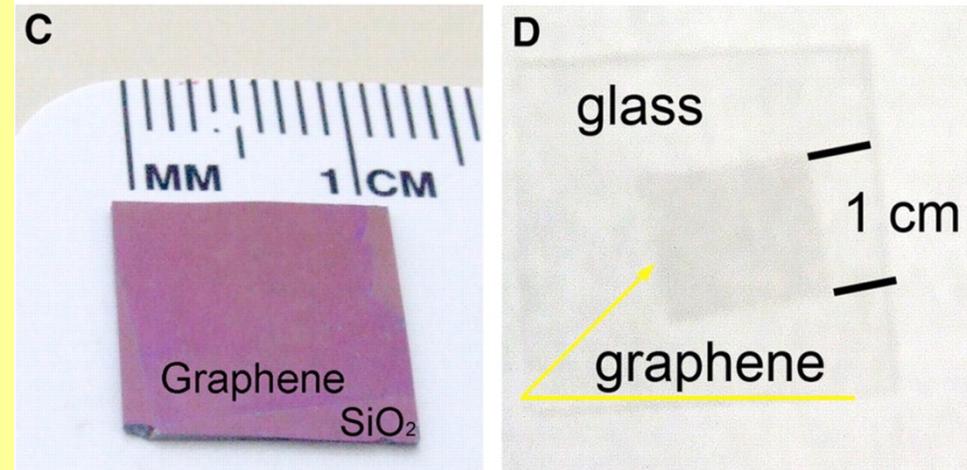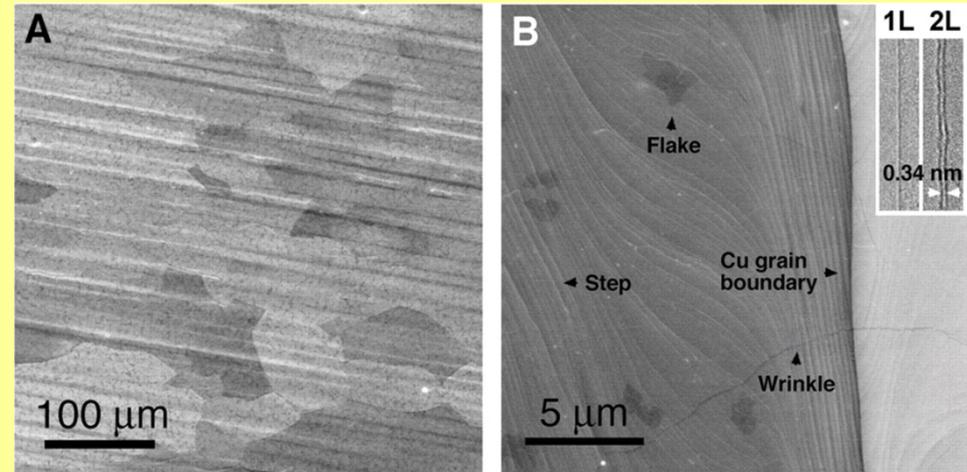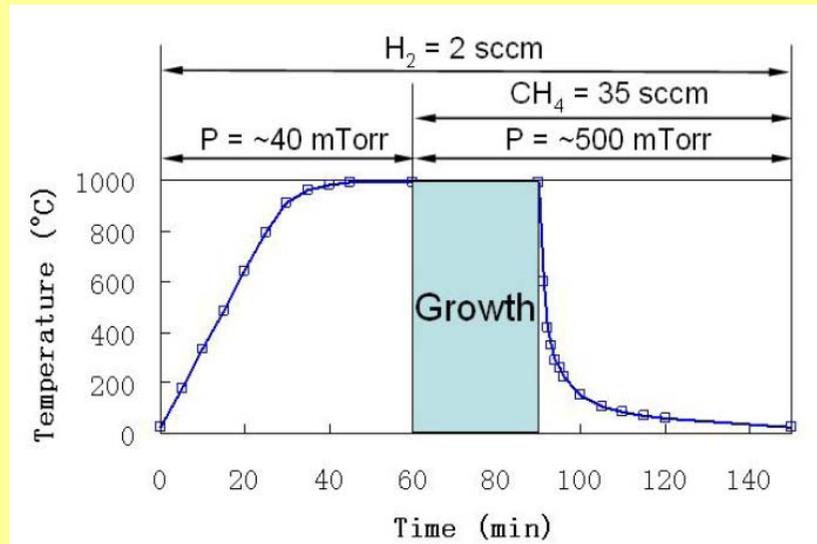

(A) SEM - graphene on a copper foil

(B) High-resolution SEM - Cu grain boundary and steps, two- and three-layer graphene flakes, and graphene wrinkles. Inset (B) TEM images of folded graphene edges. 1L, one layer; 2L, two layers.

Graphene transferred onto
(C) a SiO₂/Si substrate
(D) a glass plate

Graphene on SiO₂





Pseudo-magnetism

Graphene on platinum grown from ethylene at high temperatures. Cooled to low temperature to measure STM to a few degrees above absolute zero.

Both the graphene and the platinum contracted – but Pt shrank more, excess graphene pushed up into bubbles, size 4-10 nm x 2-3 nm

The stress causes electrons to behave as if they were subject to huge magnetic fields around 300 T

(record high in a lab, max 85 T for a few ms)

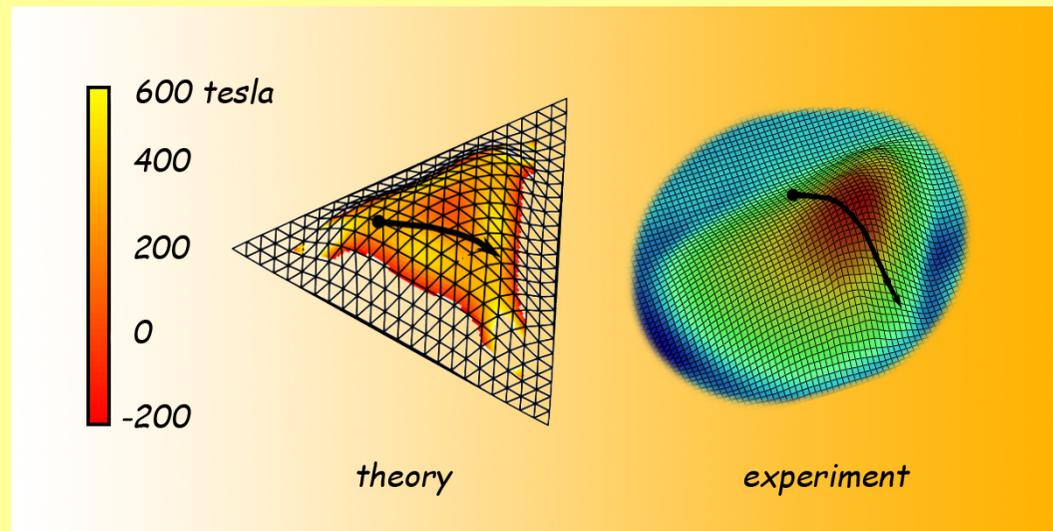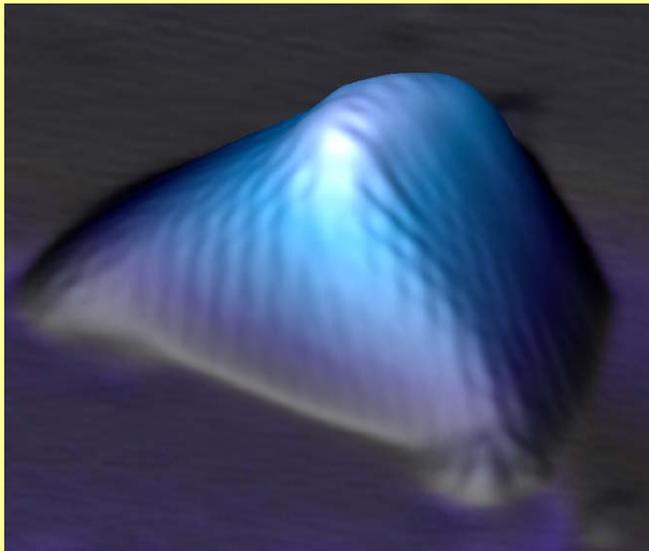

Graphene family

Graphene

hBN

BCN


Fluorographene

graphene oxide

C₃N₄



Graphene oxide

- More reactive than graphene
- Presence of oxygen groups: -OH, -COOH, =O, -O- hydrophilic character
- Electric insulator
- Specific SA (theoretically): 1700-1800 m²g⁻¹
- Hummers method

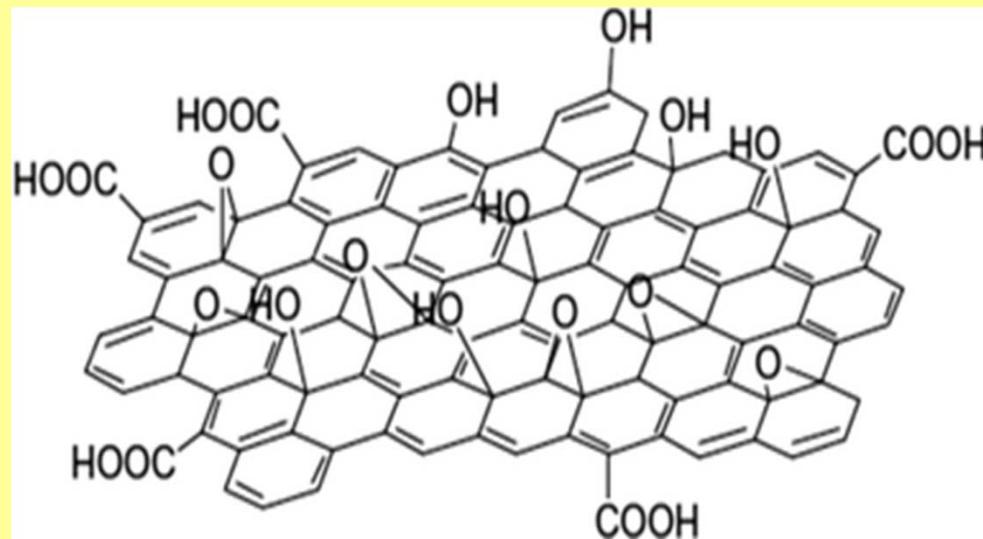


Graphane – hydrogenated graphene

- 2009 (graphene + cold hydrogen plasma)
- Two conformations: chair x boat
- Calculated binding energy = most stable compound with stoichiometric formula CH
- Chair type graphane insulating nanotubes

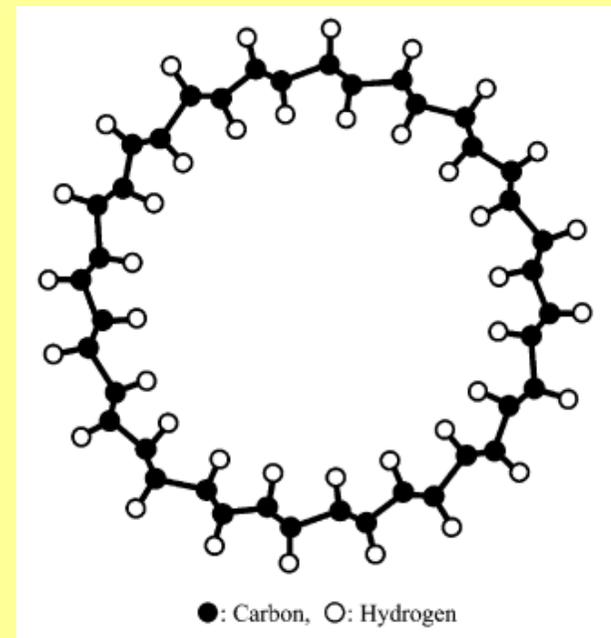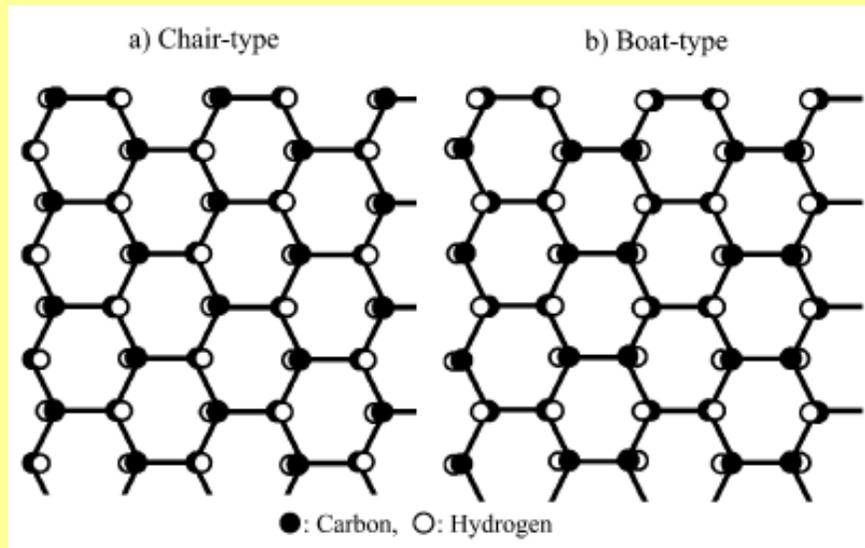


Fluorographene

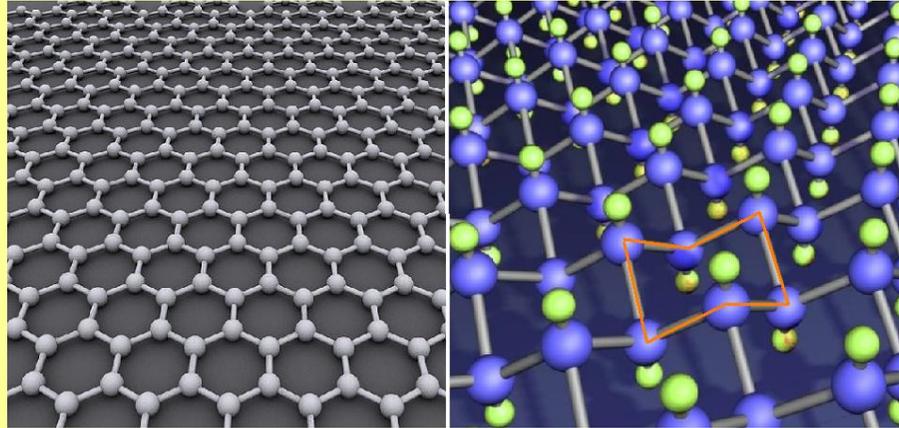


- **Monolayer of graphite fluoride**
- **Chair type x boat type-strong repulsion**
- **Synthesis:**
 - Graphene + XeF_2/CF_4 (room temperature)
 - Mechanical or chemical exfoliation of graphite fluoride
 - By heating graphene in XeF_2 gas at 250 °C
- **Graphene + XeF_2 at 70 °C – high-quality insulator, stable up to 400 °C (resemblance with teflon)**

Graphyn, graphydiyn

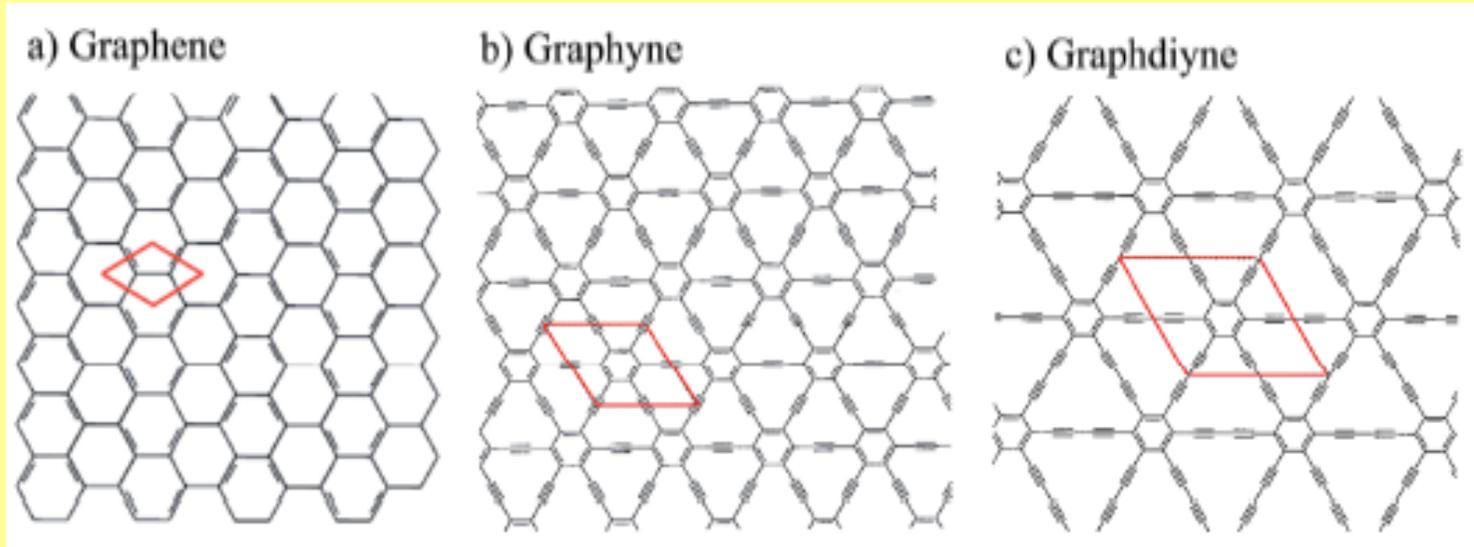

- **Predicted**
- **“Non-derivatives“ of graphene**
- **Semiconductors**
- **Movement of electrons as in graphene but only in one direction**

Graphitic carbon nitride


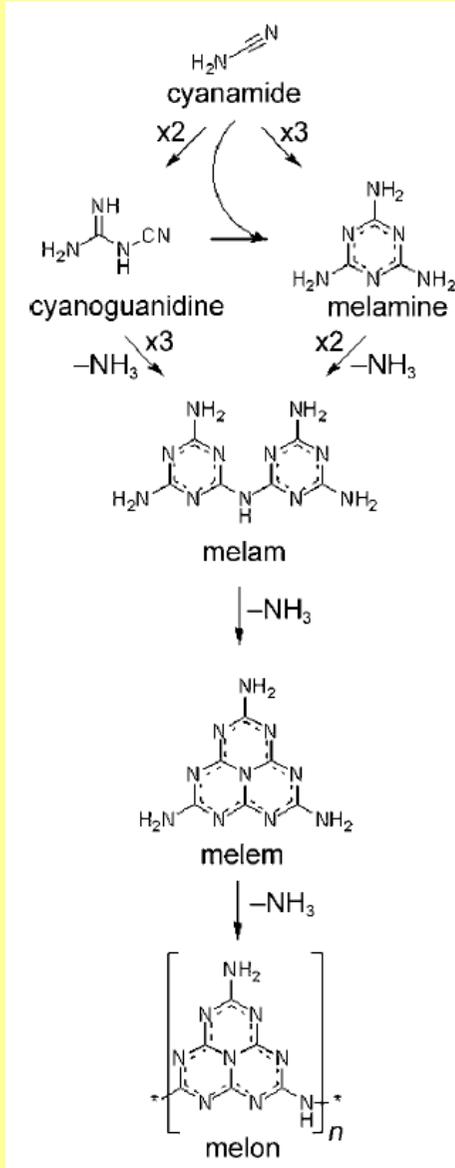


1834 Berzelius, Liebig


Temperature-induced condensation

dicyandiamide
 $\text{NH}_2\text{C}(\text{=NH})\text{NHCN}$


In a LiCl/KCl melt

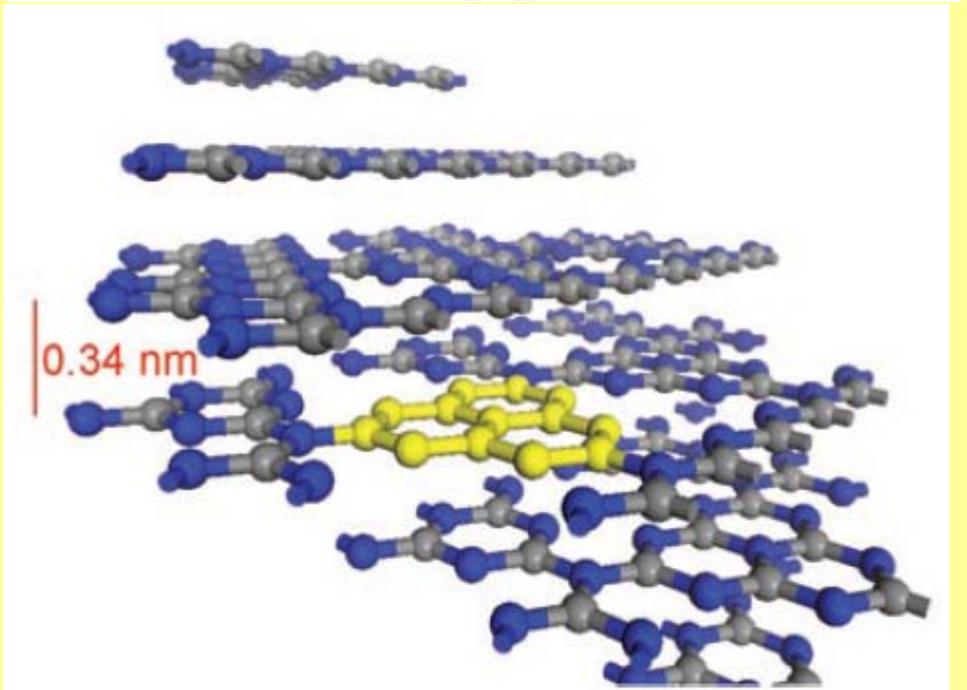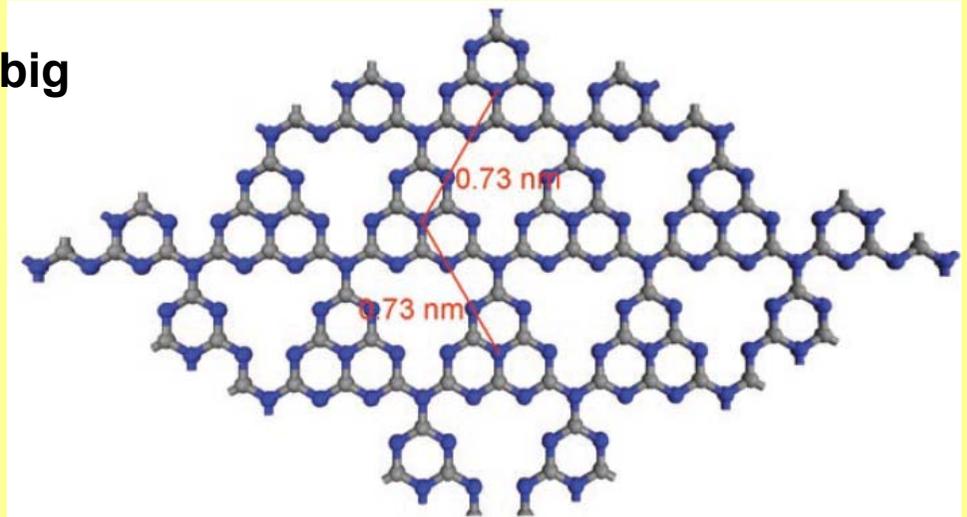


Graphitic carbon nitride

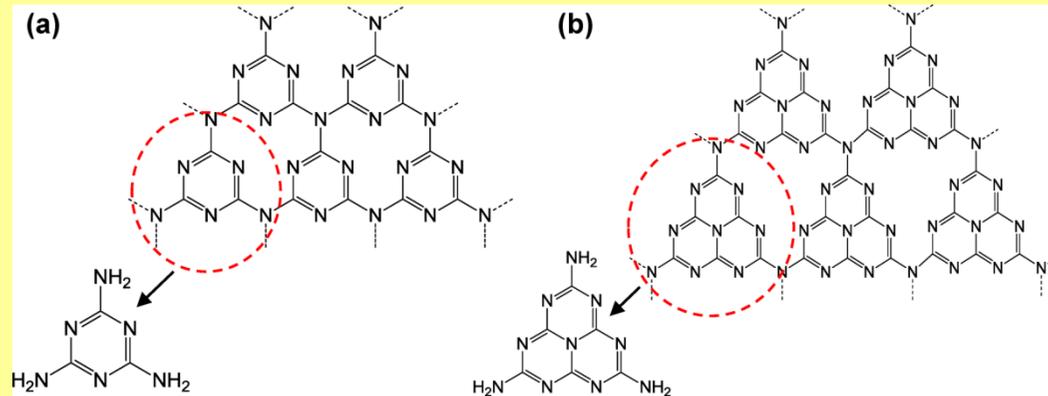


(a) triazine and (b) tri-s-triazine (heptazine)

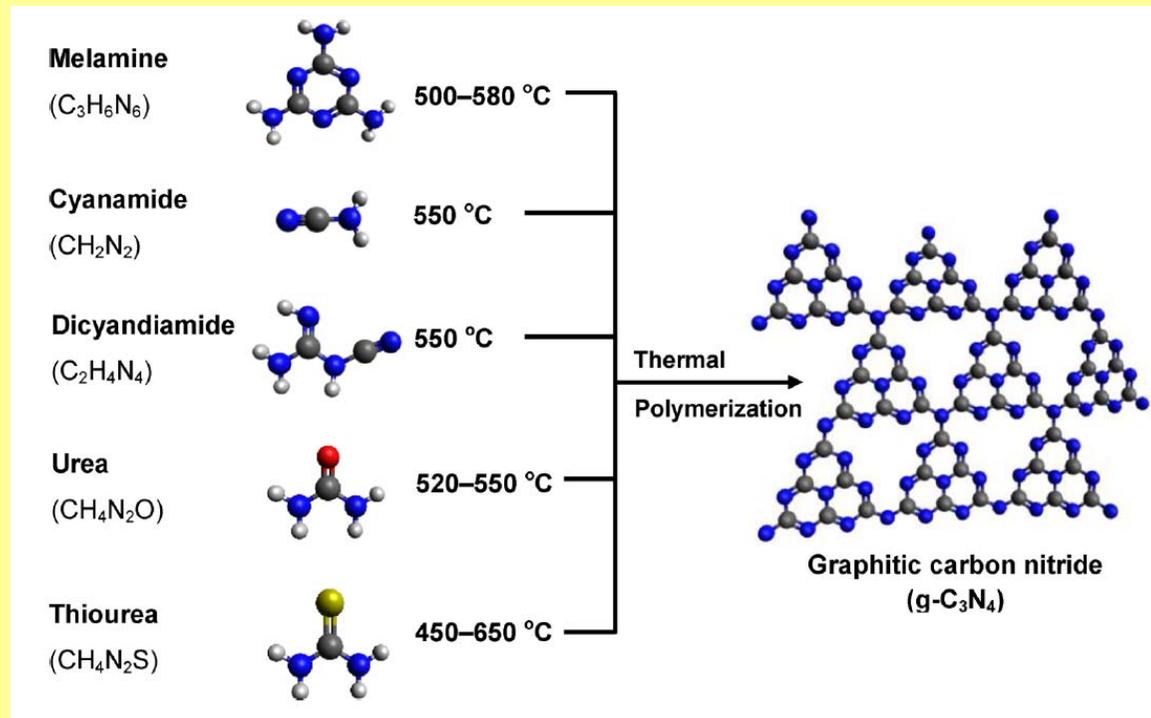

Graphitic carbon nitride

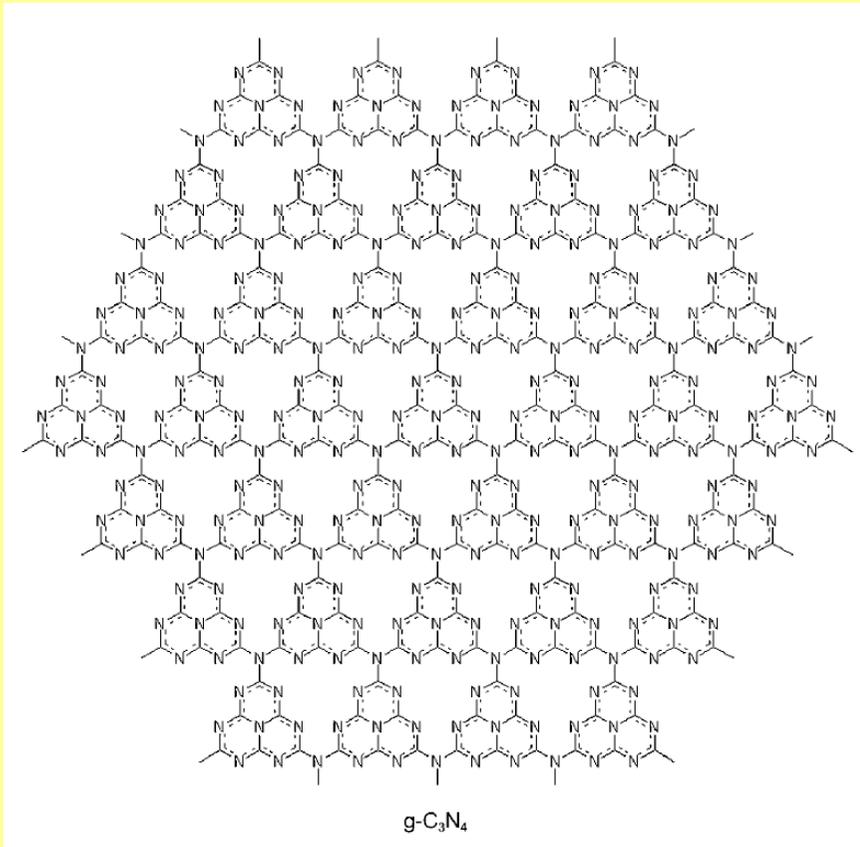


(“g-C₃N₄”)

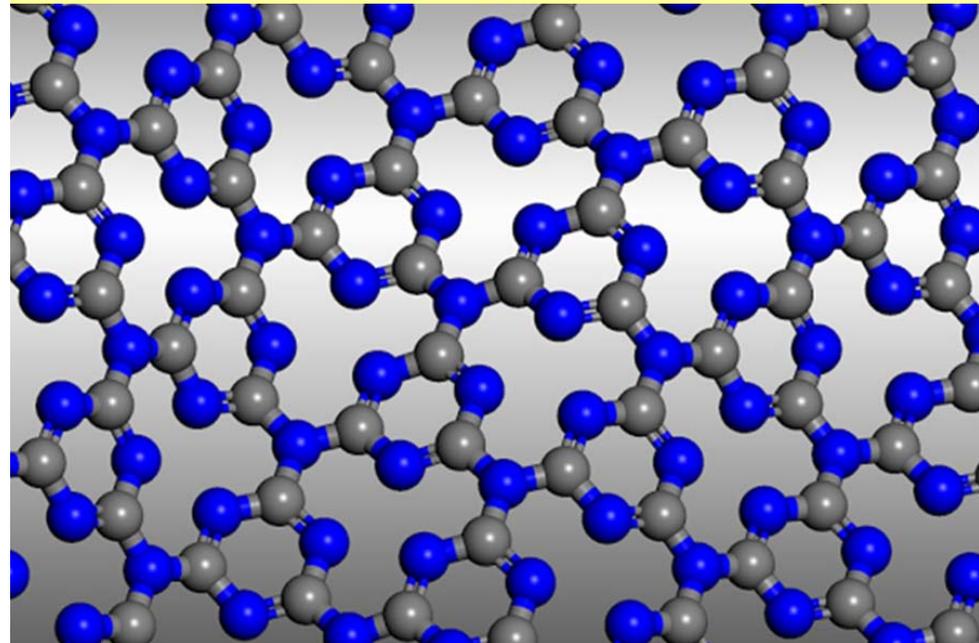

band gap 1.6 - 2.0 eV
small band gap semiconductors
Si (1.11 eV), GaAs (1.43 eV), and GaP (2.26 eV)

Phosphorene

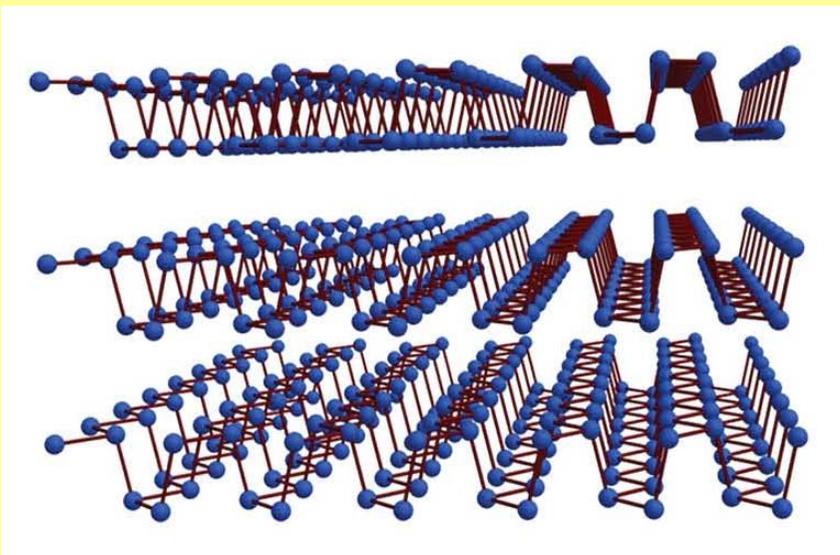

Black phosphorus


Orthorhombic

$a = 3.31 \text{ \AA}$, $b = 4.38 \text{ \AA}$, $c = 10.50 \text{ \AA}$

$\alpha = \beta = \gamma = 90^\circ$

Space group *Bmab*

Exfoliation

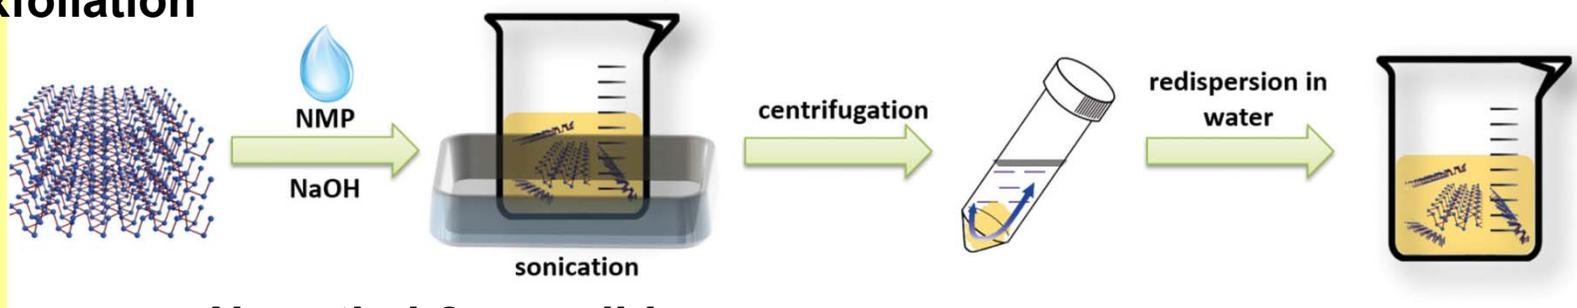

N-methyl-2-pyrrolidone





Semiconductor - direct band gap

bulk BP 0.3 eV


monolayer phosphorene 1.5 eV

Phosphorene

Height-mode AFM images
single-layer phosphorene
ca. 0.9 nm

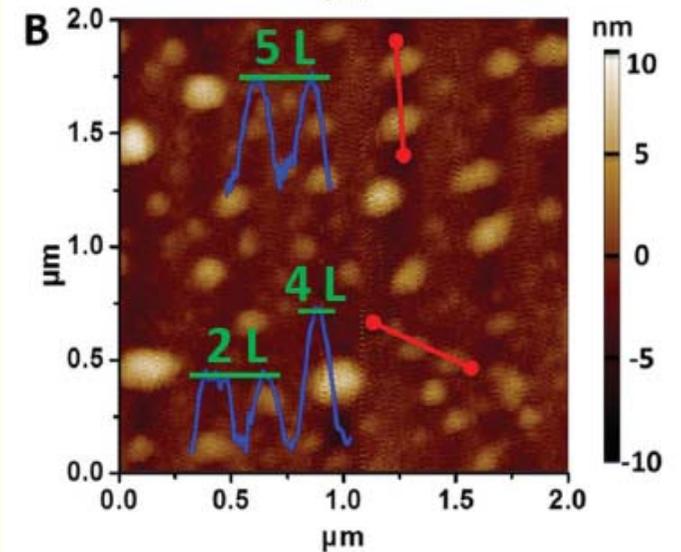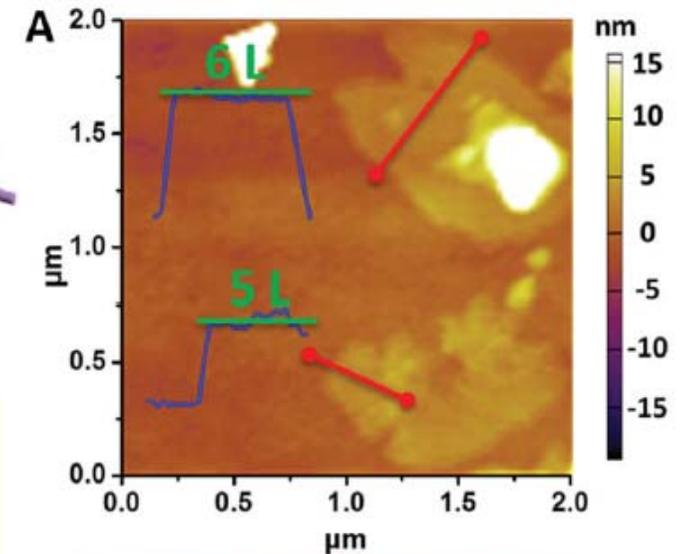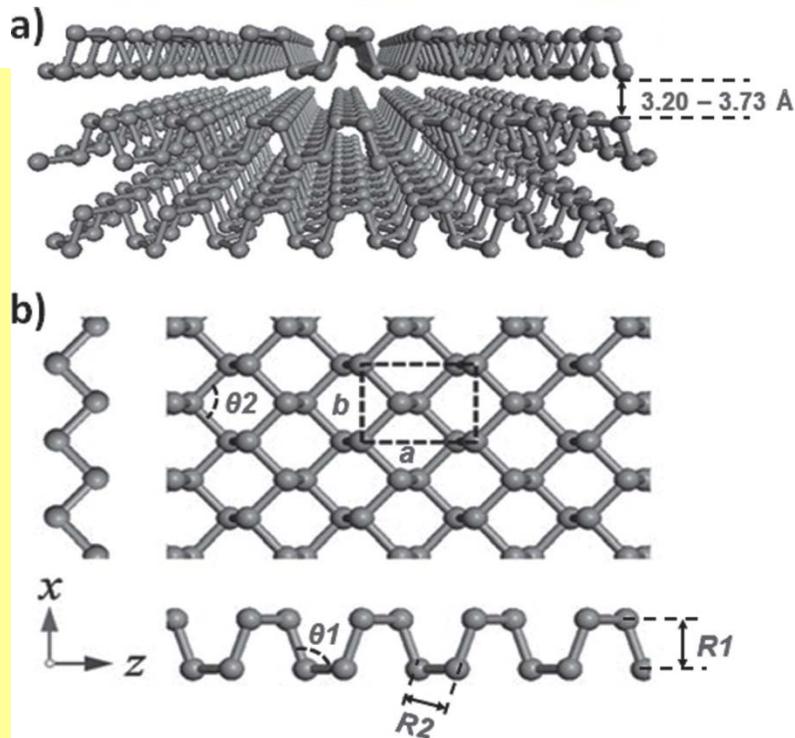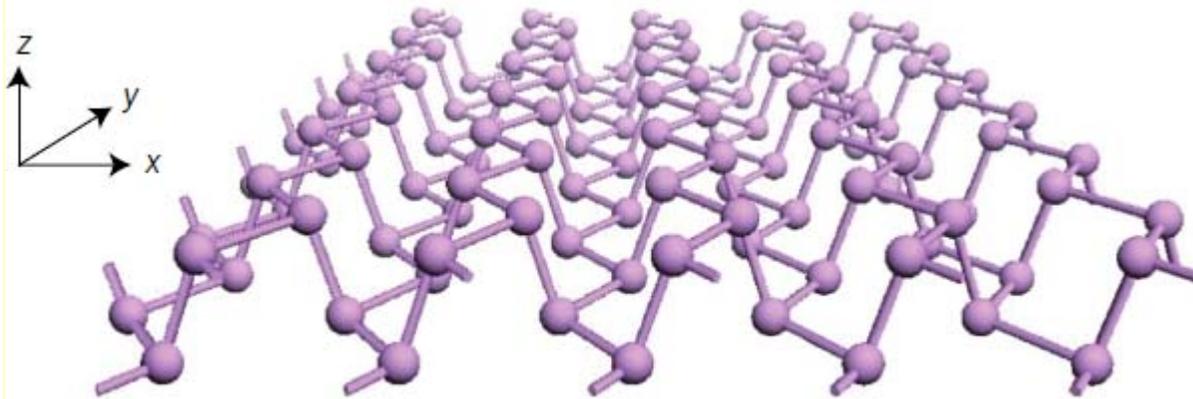

Phosphorene

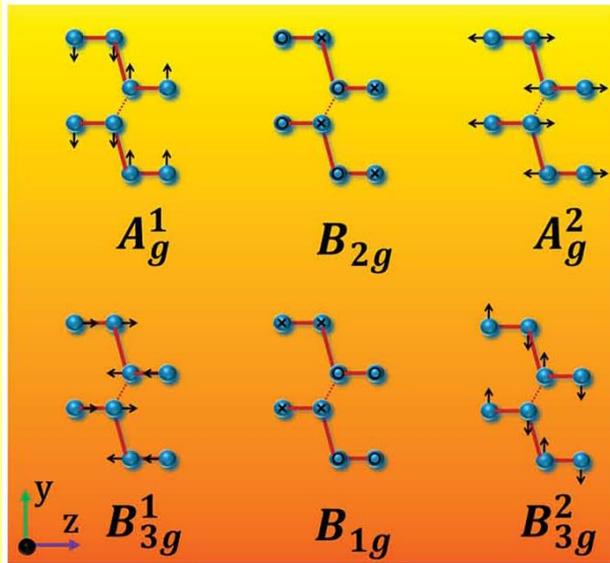



Black phosphorus

12 lattice vibrational modes


6 Raman active modes

3 vibrational modes A_{1g}^1 , B_{2g} , and A_{2g}^2 can be detected when the incident laser is perpendicular to the layered phosphorene plane: 361 cm^{-1} , 438 cm^{-1} , 465 cm^{-1}

As the number of phosphorene layers increases, the three Raman peaks red-shift

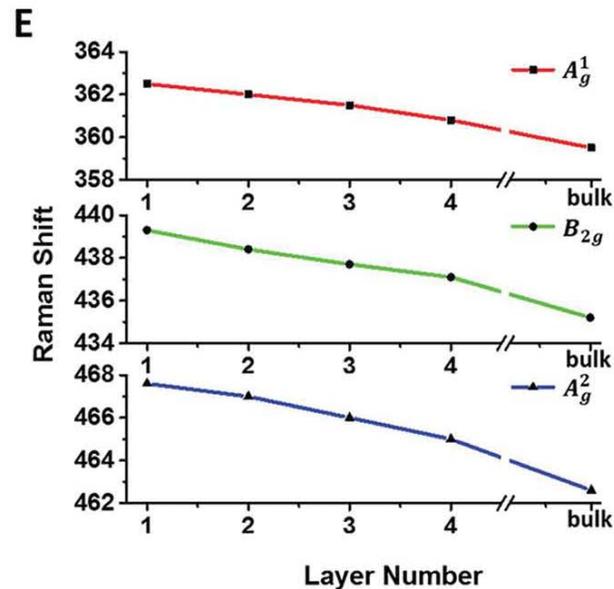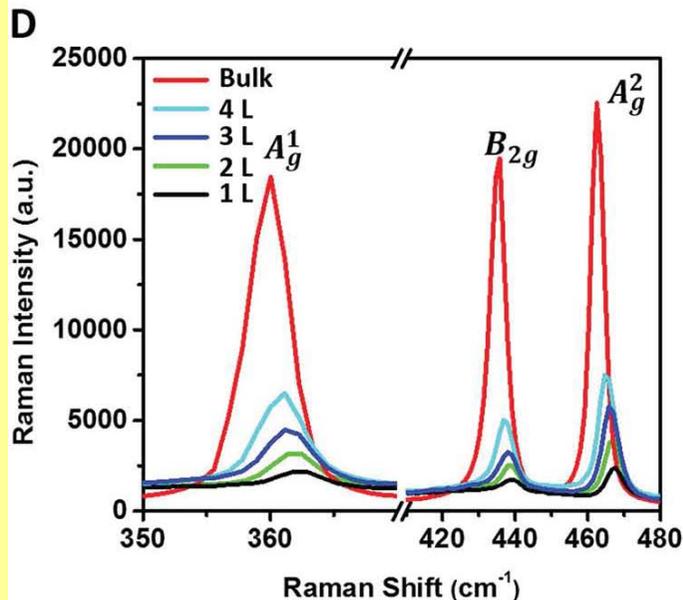


Layered Compounds - Zirconium Phosphates

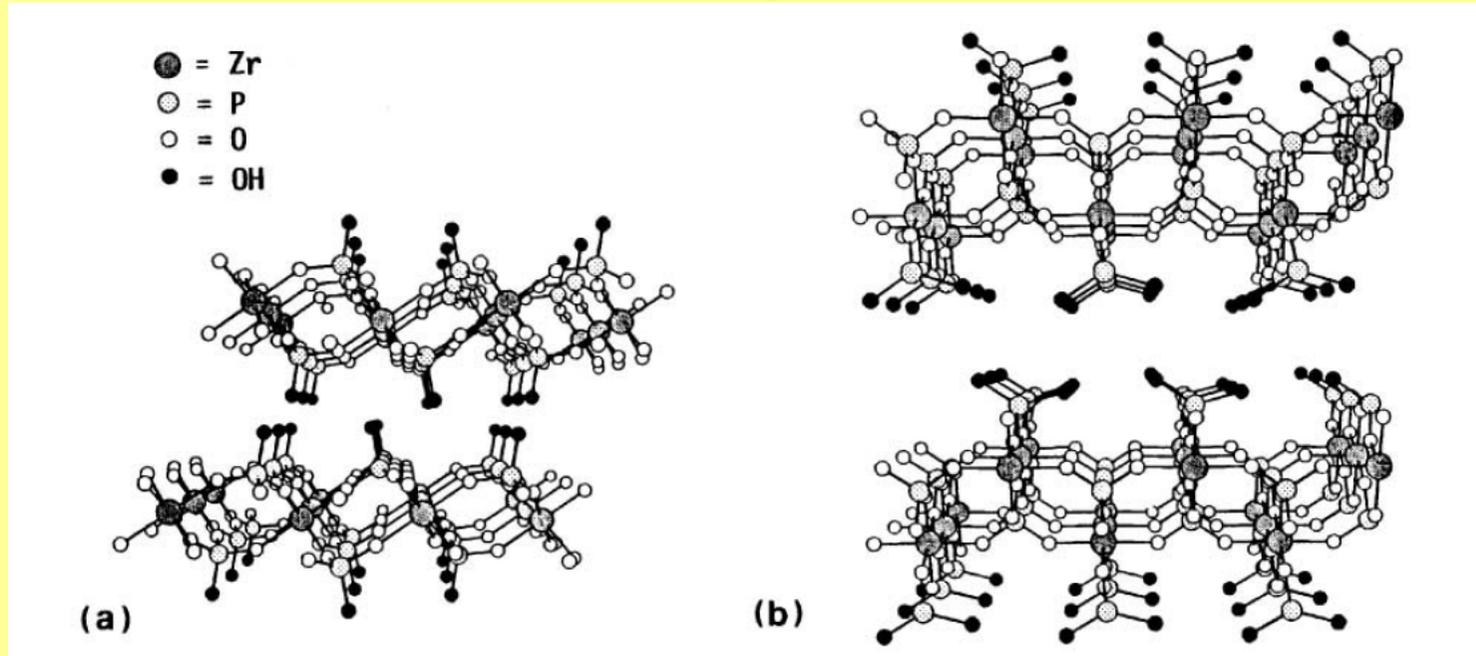

(a) α -zirconium phosphate = $\text{Zr}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$
interlayer spacing 7.6 Å

(b) γ -zirconium phosphate = $\text{Zr}(\text{PO}_4)(\text{H}_2\text{PO}_4)_2 \cdot 2\text{H}_2\text{O}$
interlayer spacing 12.2 Å


Layered Compounds - Zirconium Phosphates

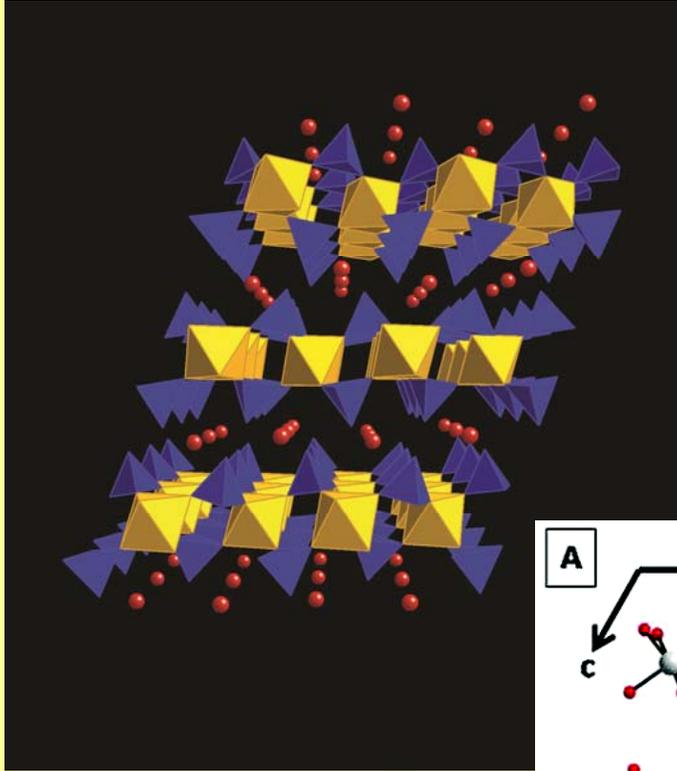


α -zirconium phosphate



interlayer spacing 7.6 Å

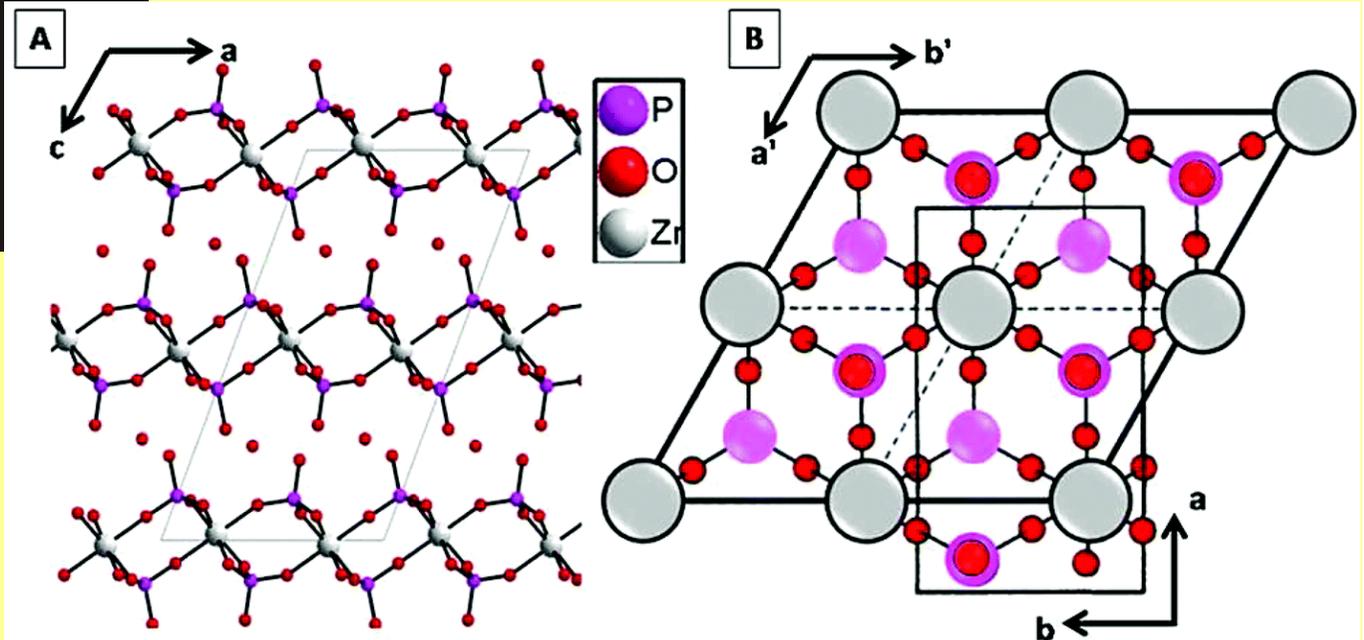


Layered Compounds - Zirconium Phosphates

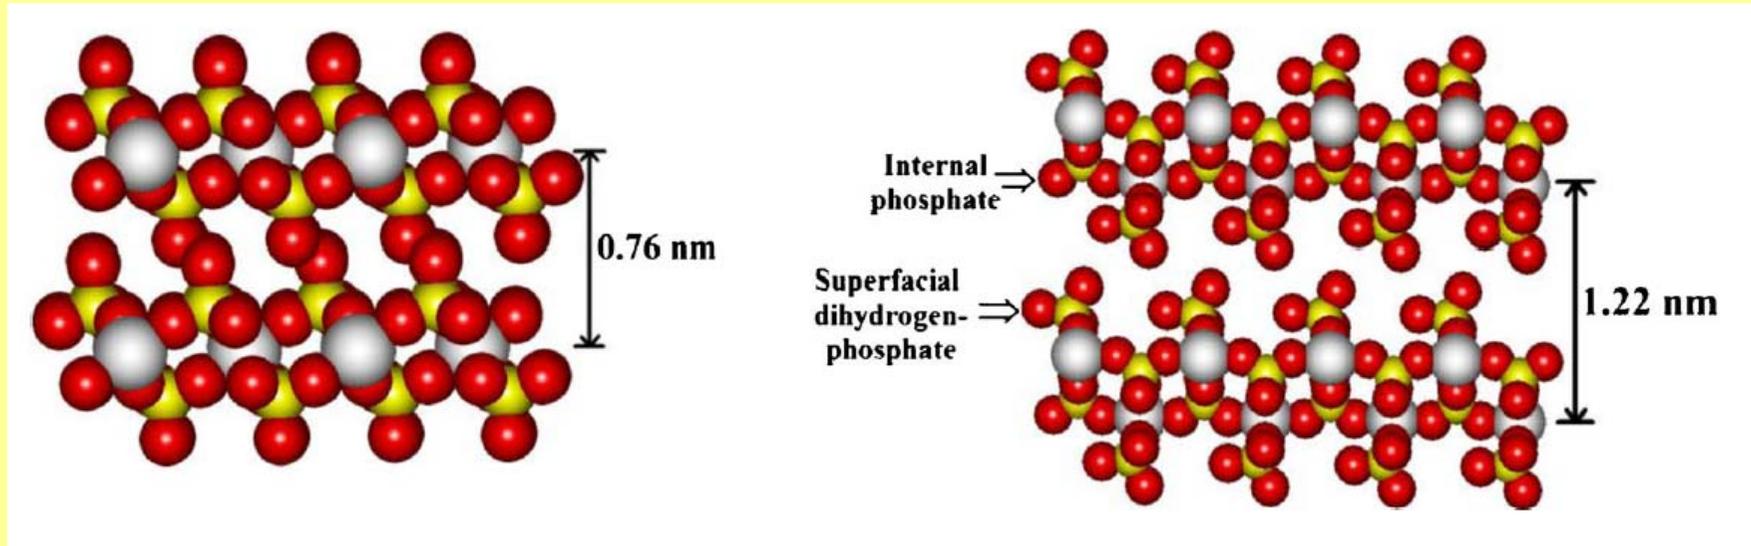

(a) α -zirconium phosphate = $\text{Zr}(\text{HPO}_4)_2 \cdot \text{H}_2\text{O}$
interlayer spacing 7.6 Å

(b) γ -zirconium phosphate = $\text{Zr}(\text{PO}_4)(\text{H}_2\text{PO}_4)2\text{H}_2\text{O}$
interlayer spacing 12.2 Å

Clay Minerals

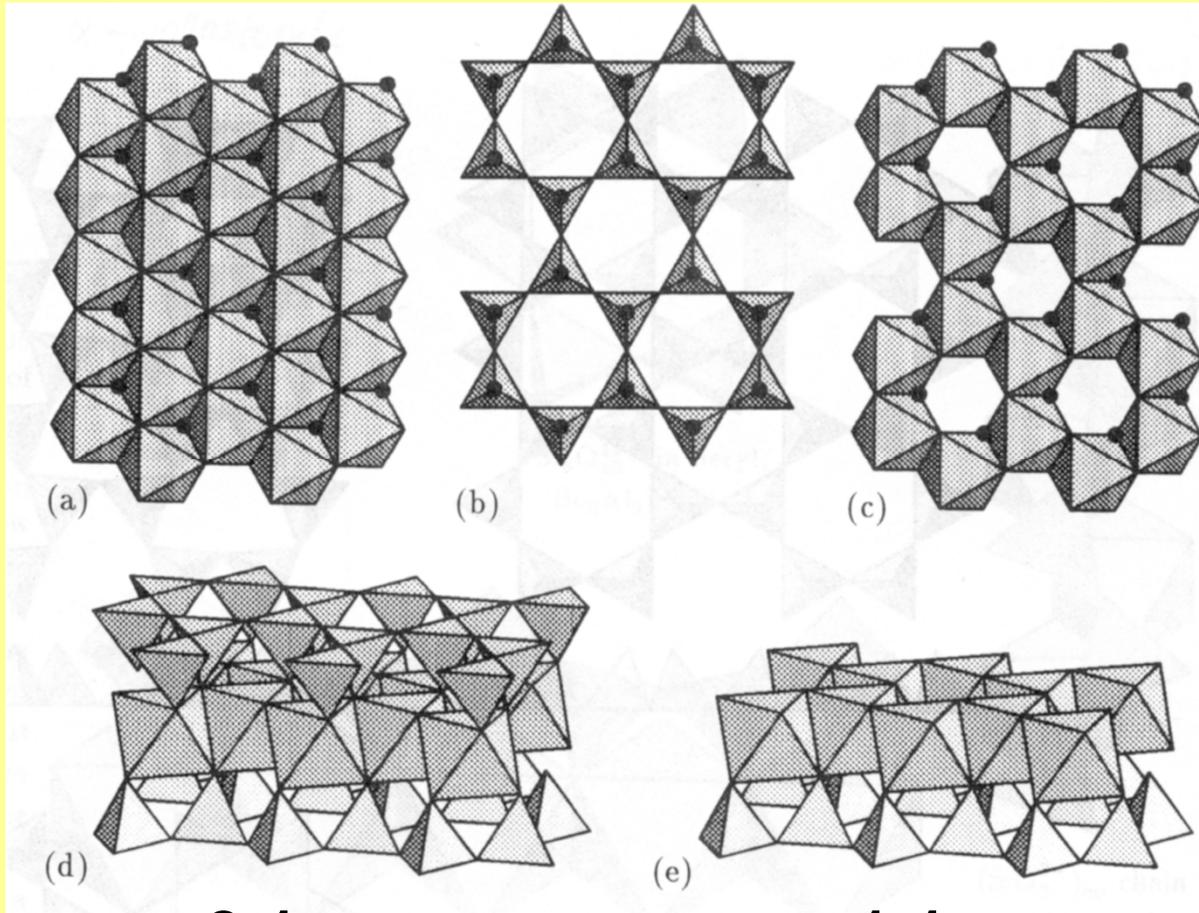


2:1

montmorillonite


1:1

kaolinite


Montmorillonite

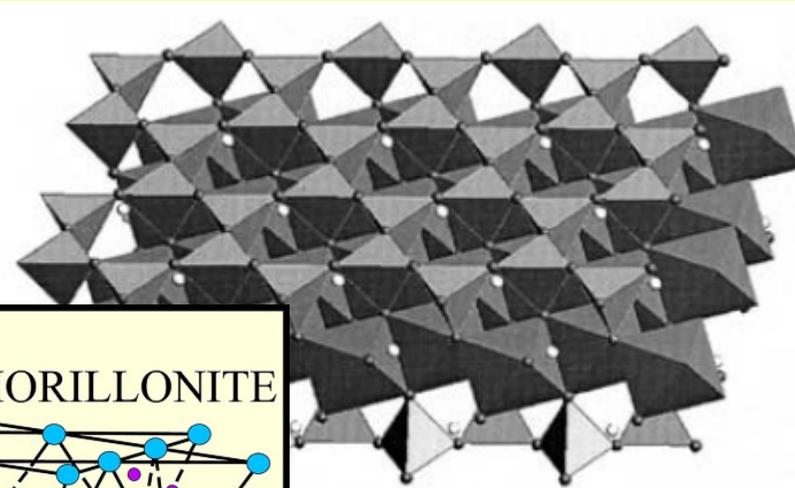

- Dioctahedral clay mineral
- $T_d-O_h-T_d$ sandwich
- Isomorphous substitution



- Net negative charge
- Interlayer cations

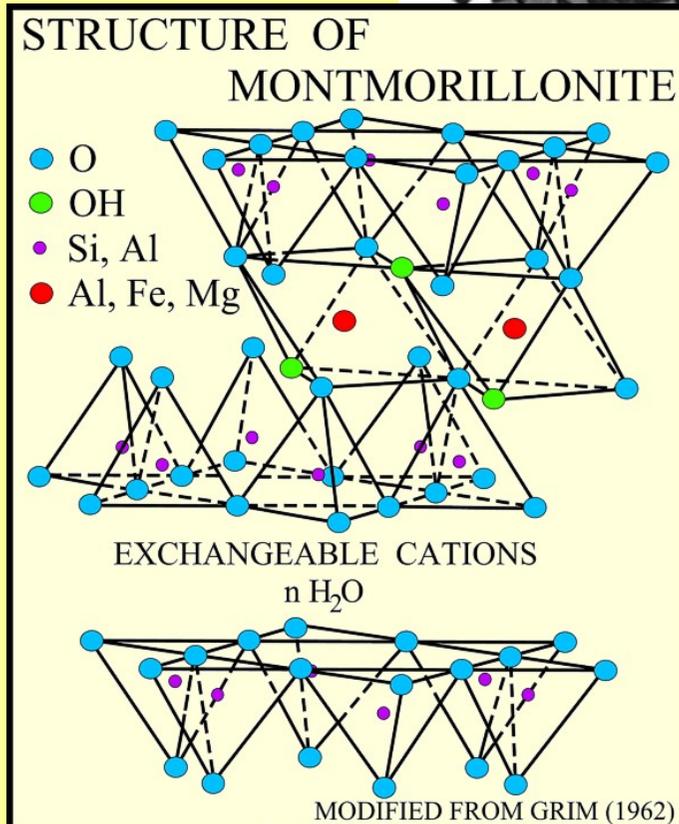


Clay Minerals

A clay $[\text{Si}_4\text{O}_{10}]^{4-}$ tetrahedral (T) sheet in (a) top view and (b) side view

A clay octahedral (O) sheet (c) top view and (d) side view

The $[\text{Al}_4\text{O}_{12}]^{12-}$ dioctahedral top view is shown in (c)

$[\text{Mg}_6\text{O}_{12}]^{12-}$ trioctahedral top view would show a continuous sheet of octahedral units

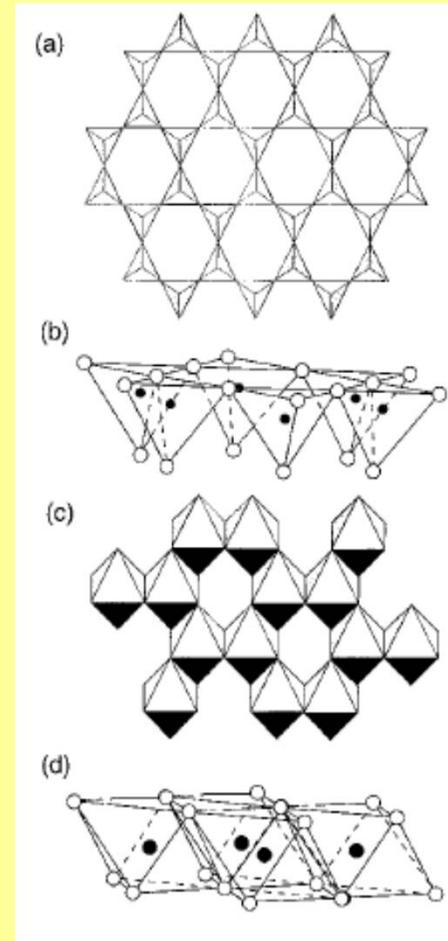

Clay Minerals

N₂ sorption isotherms


(a) TMA- and Ca-montmorillonite

(b) An Italian sepiolite

(c) Natural SHCa-1 Na-hectorite

(d) synthetic laponite and Li-(silane)-hectorites

Closed symbols = adsorption
Open symbols = desorption

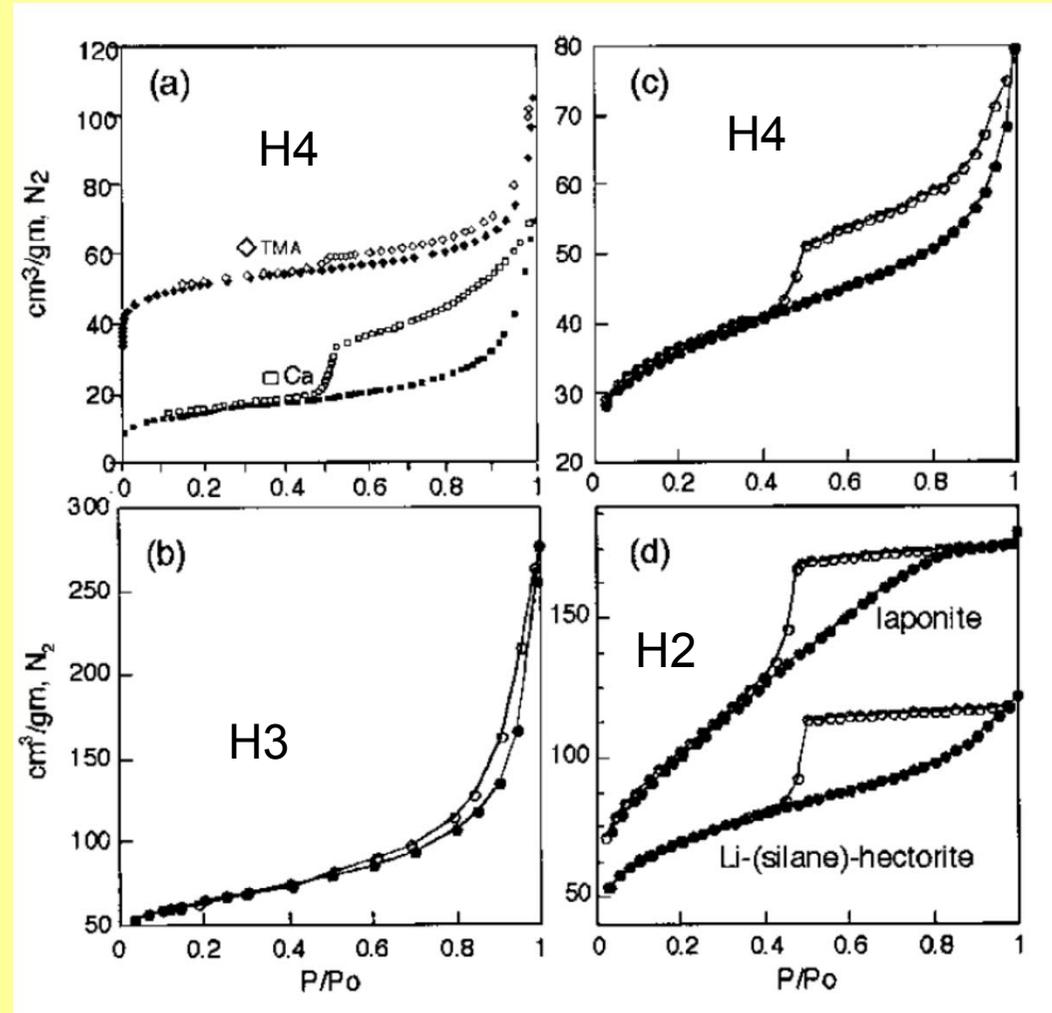

Surface Area

the most important parameters of clays with respect to catalytic applications

TABLE 3 N₂ BET Surface Areas of Various Clay Minerals

Clay	Outgassing conditions	S. A., m ² /g
Kaolinite ^{a,b}	200 °C, overnight, <10 ⁻² torr	8.75
Na,Ca-montmorillonite ^{a,c}	same	31.0
Ca-montmorillonite ^{a,d}	same	80.2
Ca-montmorillonite ^{a,e}	same	93.9
Na-hectorite ^{a,f}	same	64.3
Laponite ^g	105 °C, overnight, 10 ⁻³ torr	360
Sepiolite ^h	96 °C, 3 h	378
Palygorskite ^h	95 °C, <70 h	192

nonpolar guest molecules N₂ do not penetrate the interlayer regions

Na⁺ forms of smectites and vermiculites – no penetration

larger ions (Cs⁺ and NH₄⁺ keep the basal planes far enough) - limited penetration

Layered Double Hydroxides


LDH = layered double hydroxides

HT = hydrotalcites

Natural mineral hydrotalcite $\text{Mg}_6\text{Al}_2(\text{OH})_{16}\text{CO}_3 \cdot 4\text{H}_2\text{O}$

Brucite layers, Mg^{2+} substituted partially by Al^{3+}


Layers have positive charge

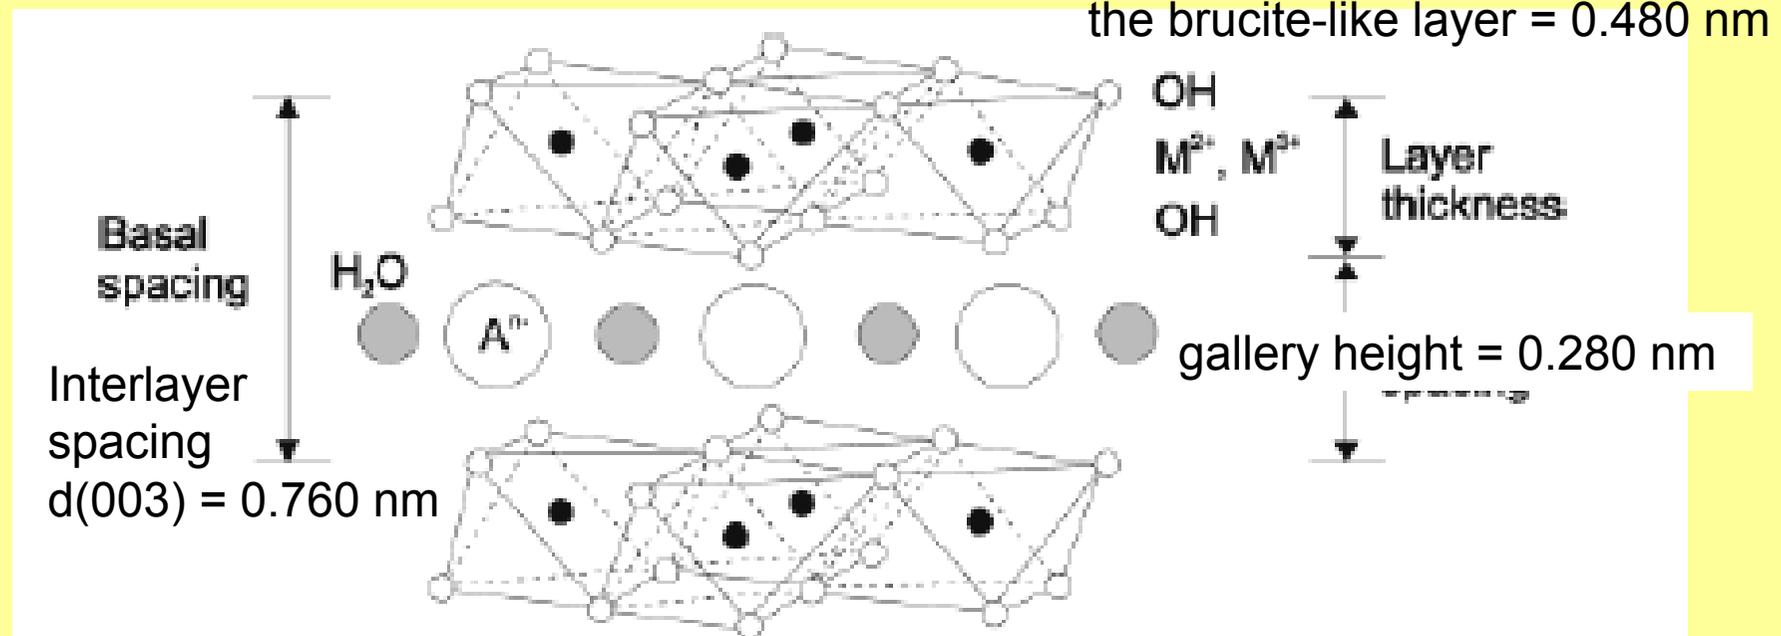

Hydrotalcite $\text{Mg}_6\text{Al}_2(\text{OH})_{16}\text{CO}_3 \cdot 4\text{H}_2\text{O}$

Hydrotalcites

Brucite layers, Mg^{2+} substituted partially by Al^{3+}
Layers have positive charge

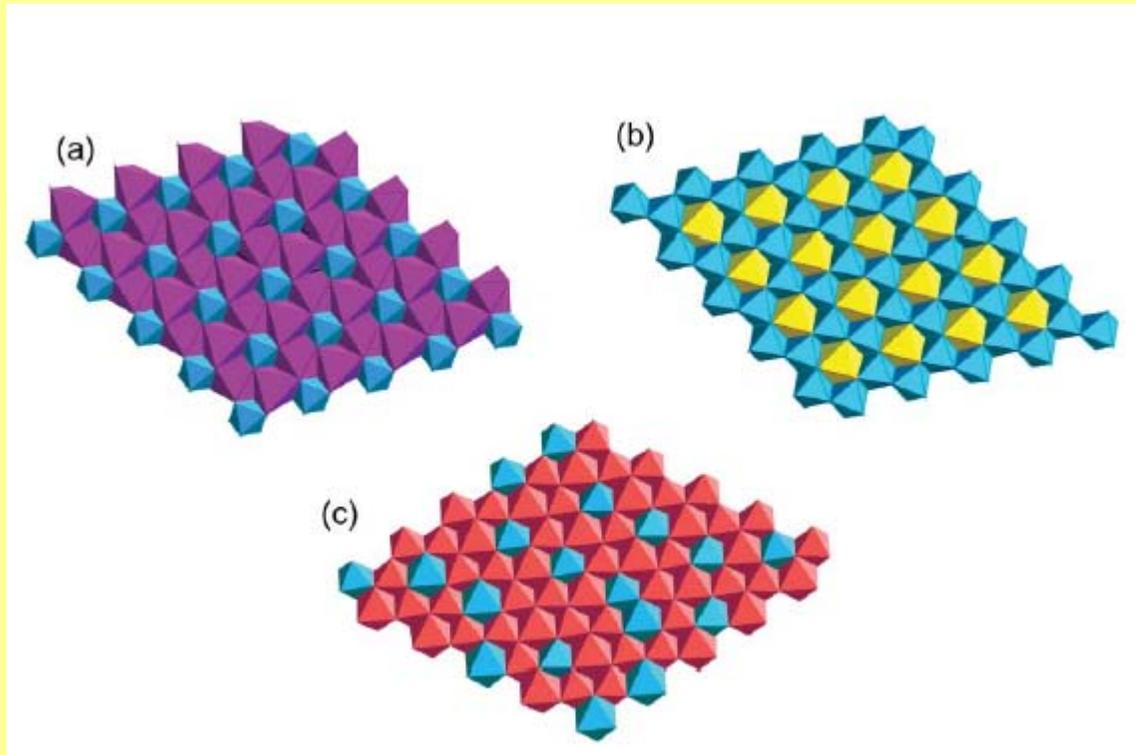

(a) $[\text{Ca}_2\text{Al}(\text{OH})_6]_2\text{SO}_4 \cdot 6\text{H}_2\text{O}$ (b) $[\text{LiAl}_2(\text{OH})_6]\text{Cl}$ (c) $[\text{Mg}_{2.25}\text{Al}_{0.75}(\text{OH})_6]\text{OH}$


Hydrotalcite

The layered structure of LDH is closely related to brucite $\text{Mg}(\text{OH})_2$

a brucite layer, Mg^{2+} ions octahedrally surrounded by six OH^-
the octahedra share edges and form an infinite two-dimensional layer

the brucite-like layers stack on top of one another
either rhombohedral (3R) or hexagonal (2H) sequence

Hydrotalcite $\text{Mg}_6\text{Al}_2(\text{OH})_{16}\text{CO}_3 \cdot 4\text{H}_2\text{O}$ - 3R stacking



Hydrotalcite


The interlayer spacing c' is equal to d_{003} , $2d_{006}$, $3d_{009}$, etc.;

$$c' = (d_{003} + 2d_{006} + \dots + nd_{00(3n)}) / n$$

The cell parameter c is a multiple of the interlayer spacing c'

$c = 3c'$ for rhombohedral (3R)

$c = 2c'$ for hexagonal (2H) sequences

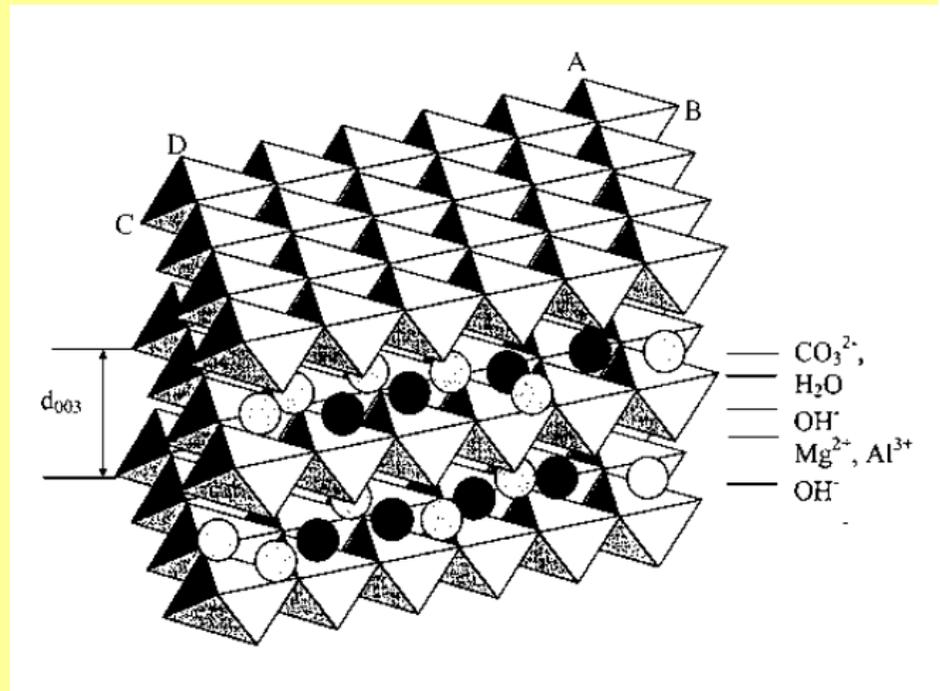

Hydrotalcite

Hydrotalcite $\text{Mg}_6\text{Al}_2(\text{OH})_{16}\text{CO}_3 \cdot 4\text{H}_2\text{O}$ - 3R stacking

unit cell parameters

$$a = 0.305 \text{ nm} \quad c = 3d(003) = 2.281 \text{ nm}$$

the interlayer spacing: $d(003) = 0.760 \text{ nm}$


the spacing occupied by the anion (gallery height) = 0.280 nm

a thickness of the brucite-like layer = 0.480 nm

the average M—O bond = 0.203 nm

the distance between two nearest OH^- ions in the two opposite side layers = 0.267 nm shorter than a (0.305 nm) and indicative of some contraction along the c -axis.


XRD Patterns of LDH

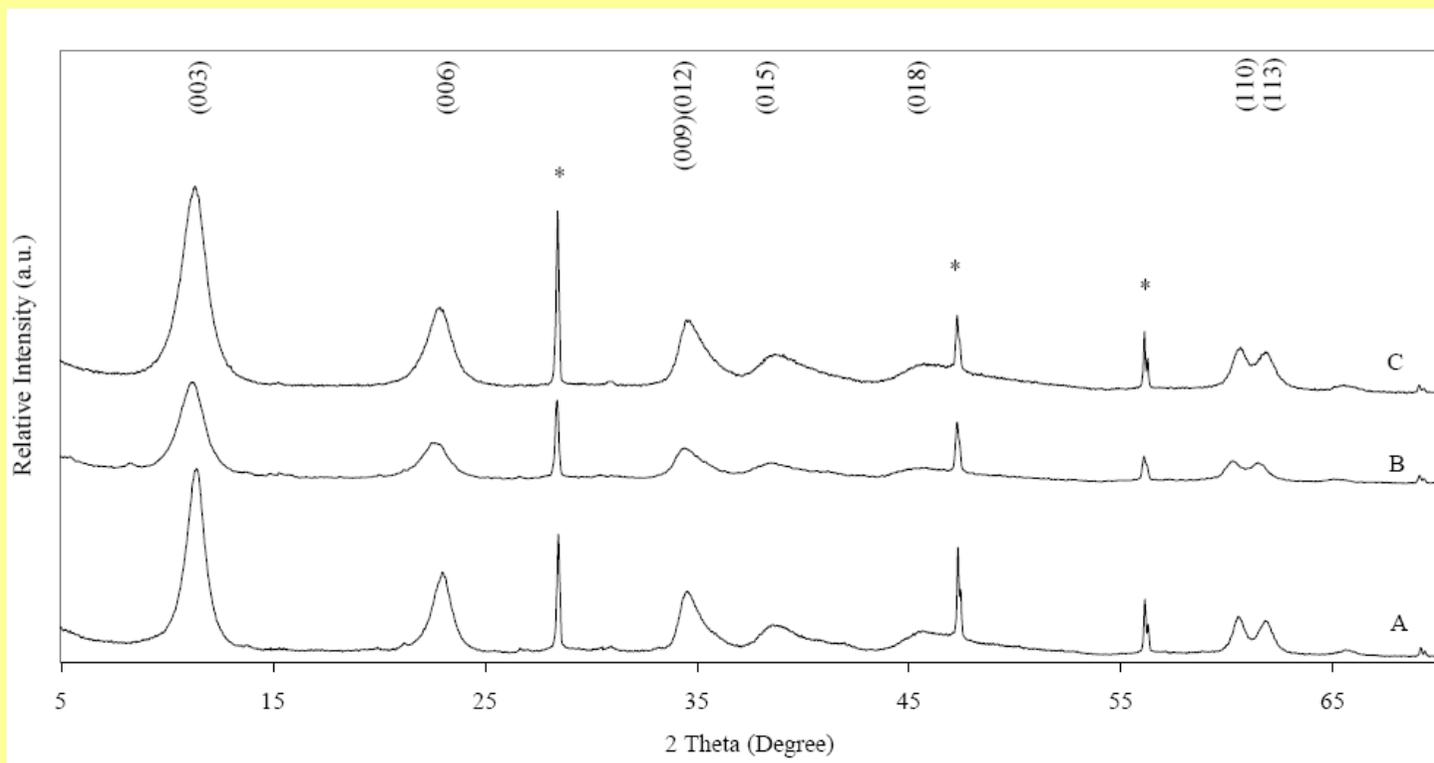

**XRD patterns of layered double hydroxides synthesized by coprecipitation method with various cations composition:
A – Mg/Al; B- Mg/Co/Al; C- Mg/Ni/Al**

*** = Reflections from Si crystal used as a reference**

XRD Patterns of LDH

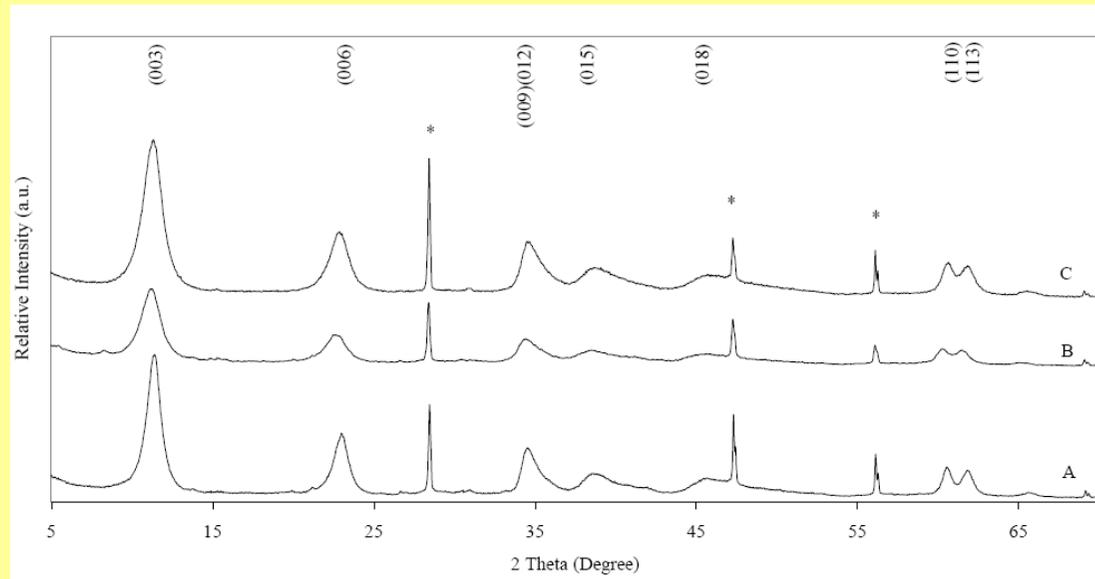

rhombohedral structure
the cell parameters c and a

The lattice parameter $a = 2d(110)$ corresponds to an average cation–cation distance

The c parameter corresponds to three times the thickness of d_{003}


$$c = 3/2 [d_{003} + 2d_{006}]$$

Layered Compounds


LDH = layered double hydroxides
hydrotalcites



Brucite layers, Mg^{2+} substituted partially by Al^{3+}

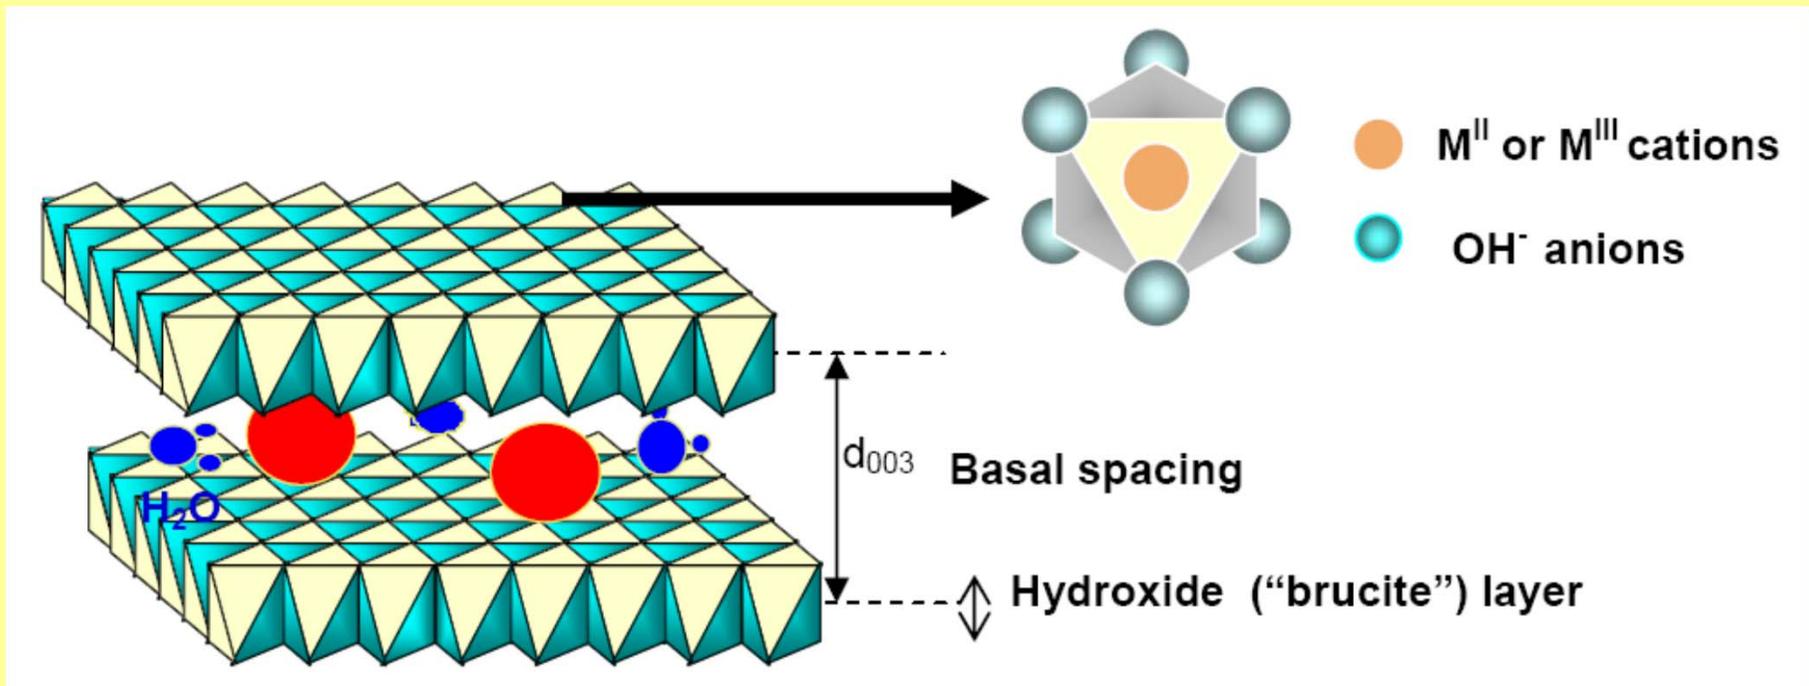

Intercalation to LDH

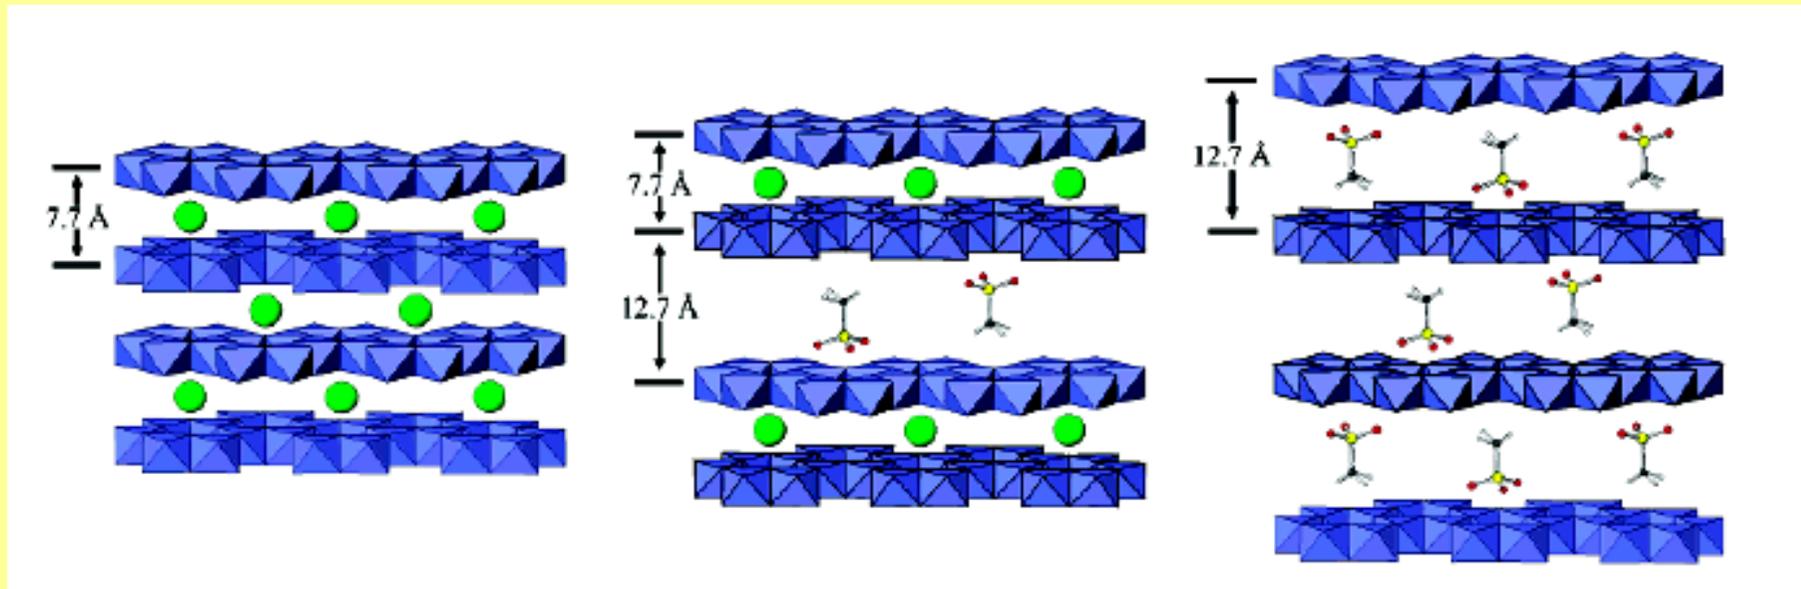

the intercalation of methylphosphonic acid into Li/Al LDH

(a) $[\text{LiAl}_2(\text{OH})_6]\text{Cl}\cdot\text{H}_2\text{O}$

(b) second-stage intermediate, alternate layers occupied by Cl and MPA anions

(c) first-stage product with all interlayer regions occupied by MPA.

Intercalation to LDH

LDH = layered double hydroxides


hydrotalcites

mineral $\text{Mg}_6\text{Al}_2(\text{OH})_{16}\text{CO}_3 \cdot 4\text{H}_2\text{O}$


Brucite layers, Mg^{2+} substituted partially by Al^{3+}

Layers have positive charge


Intercalate anions $[\text{Cr}(\text{C}_2\text{O}_4)_3]^{3-}$

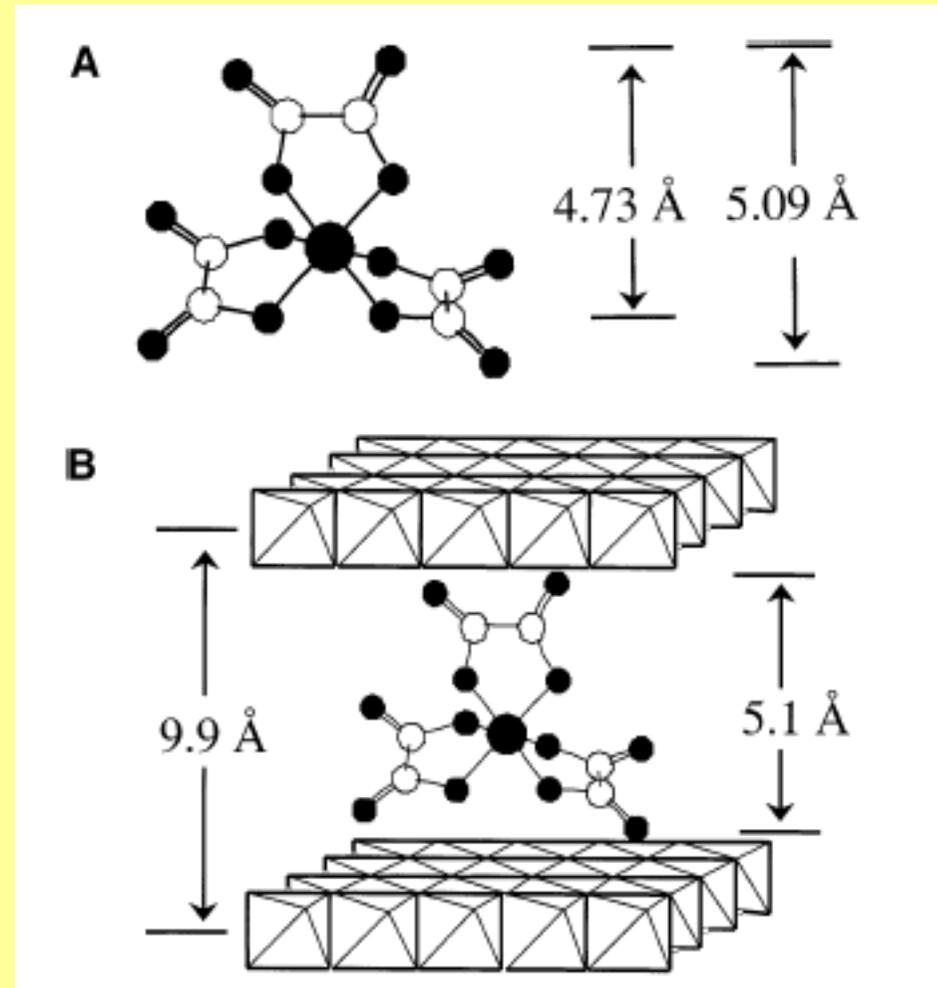


The anionic exchange capacity (AEC)

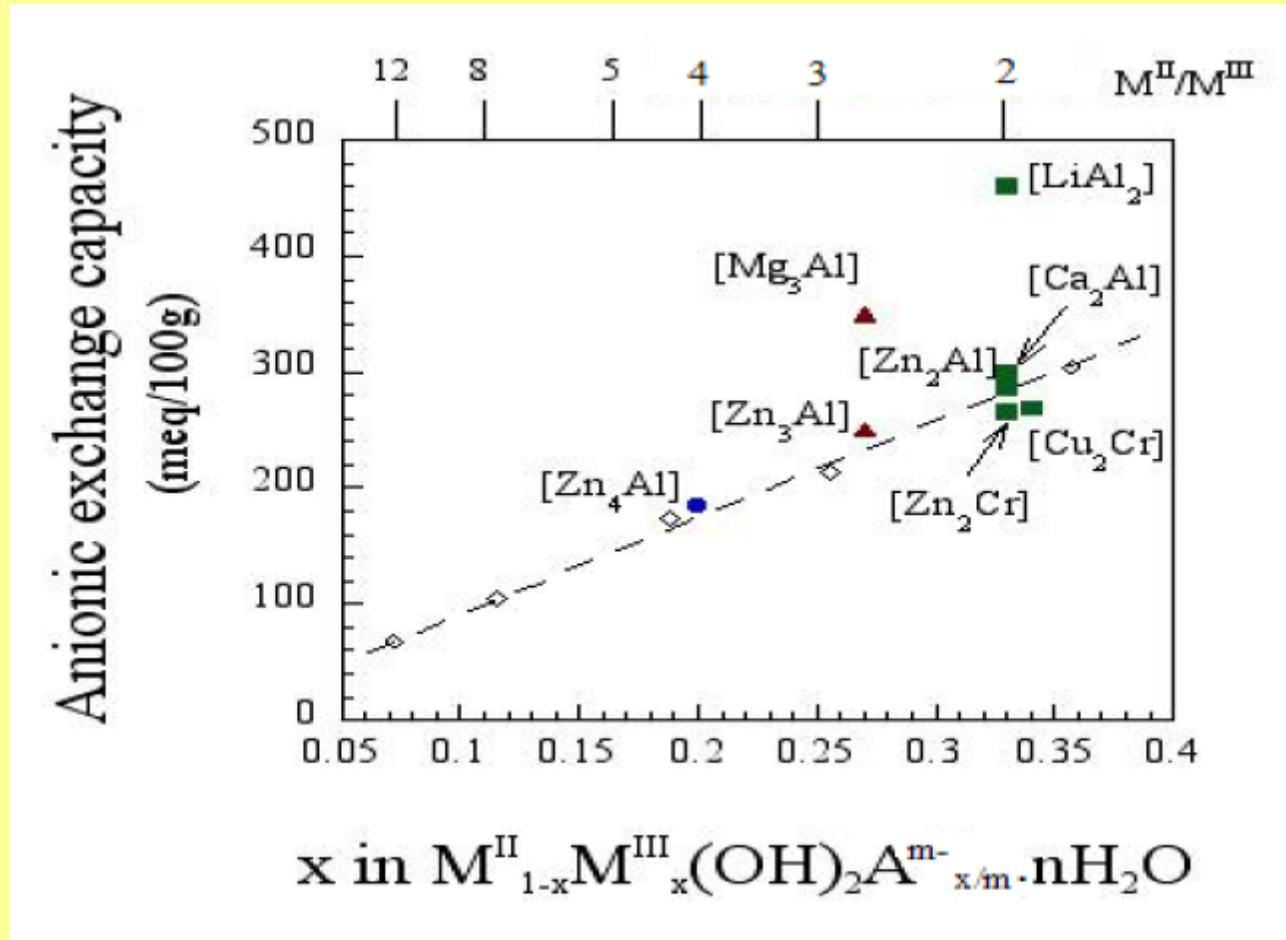



Types of the composite structures

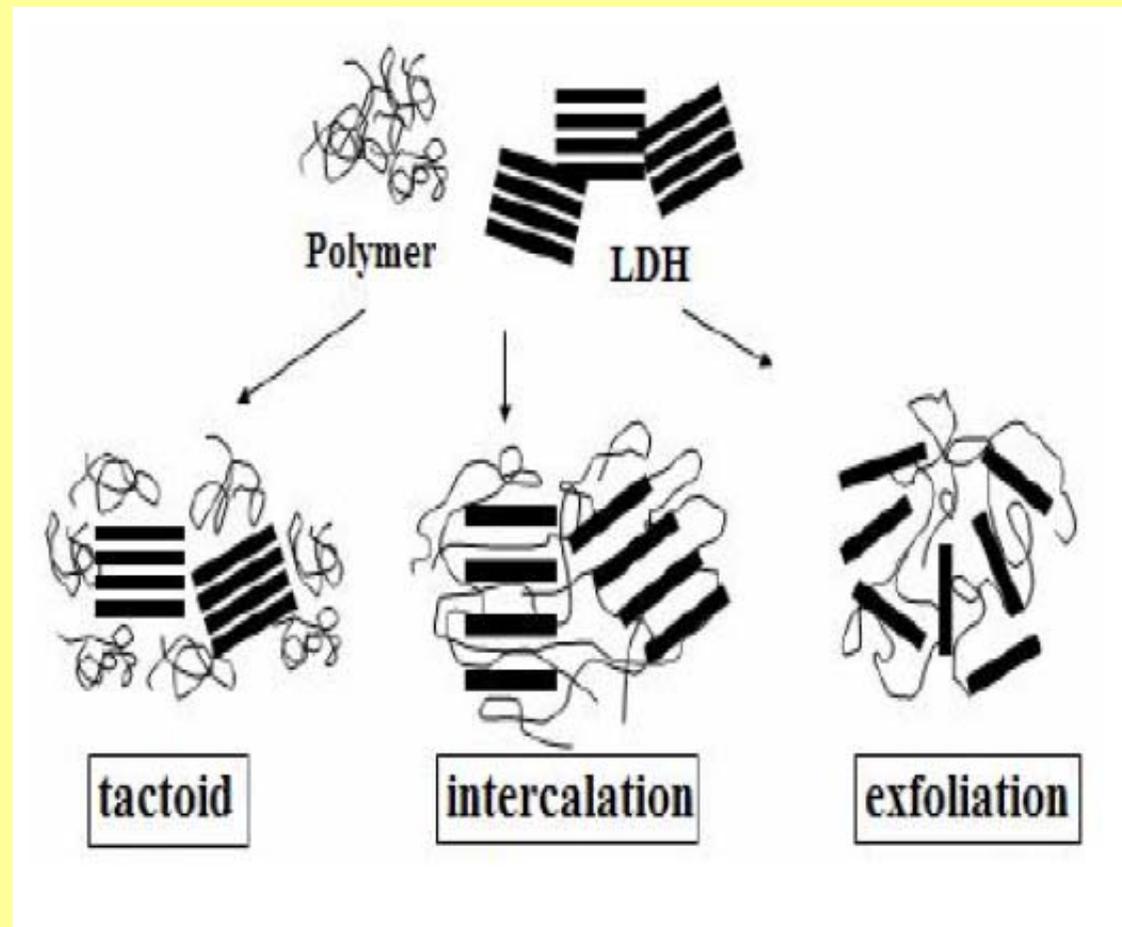



Li Intercalation Compounds

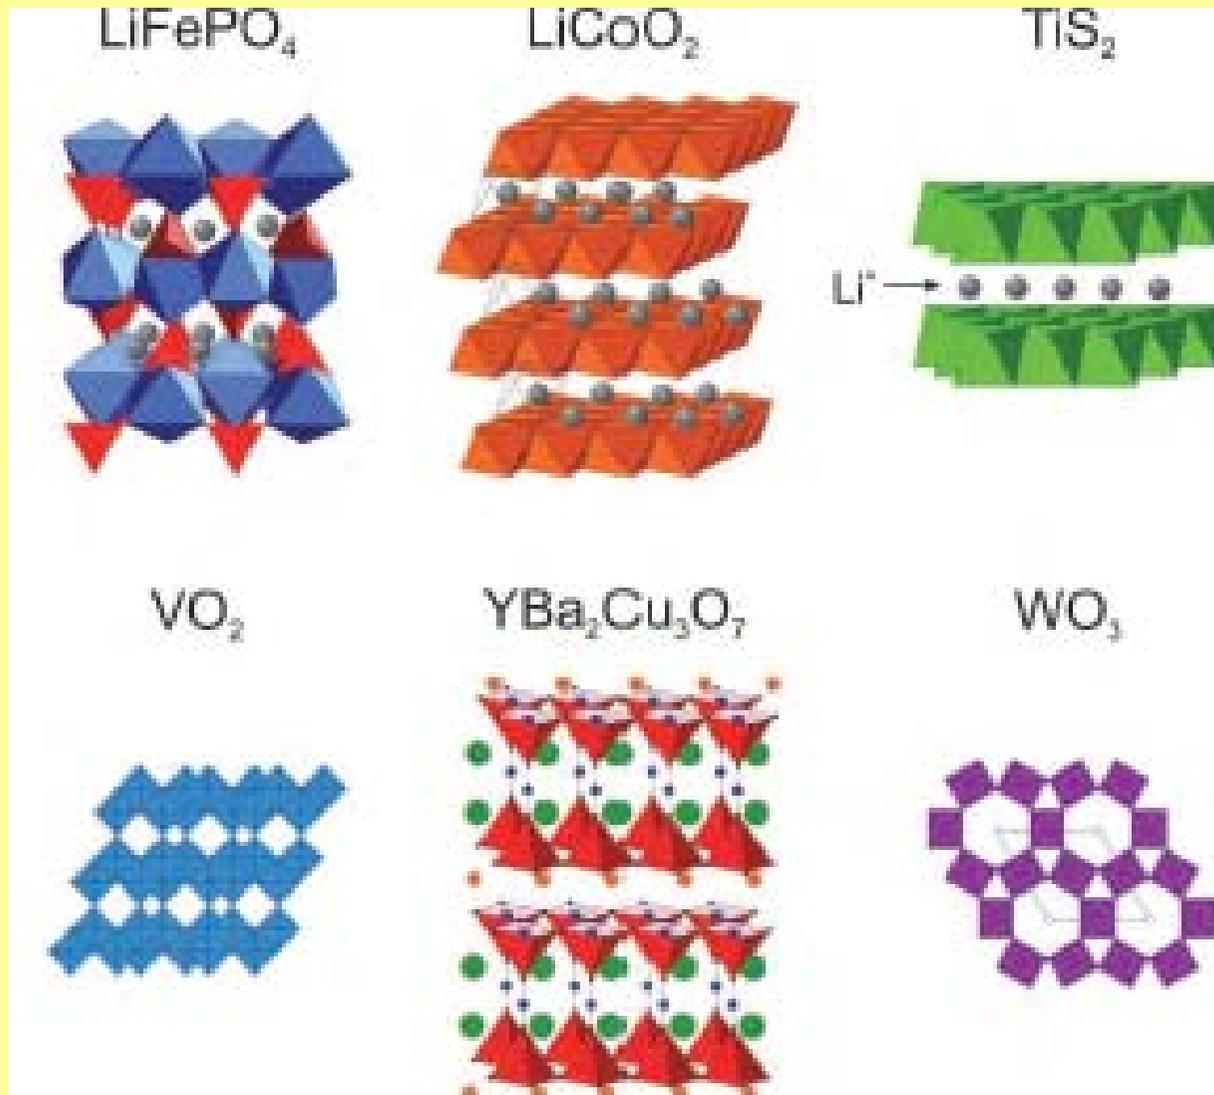

Li Intercalation

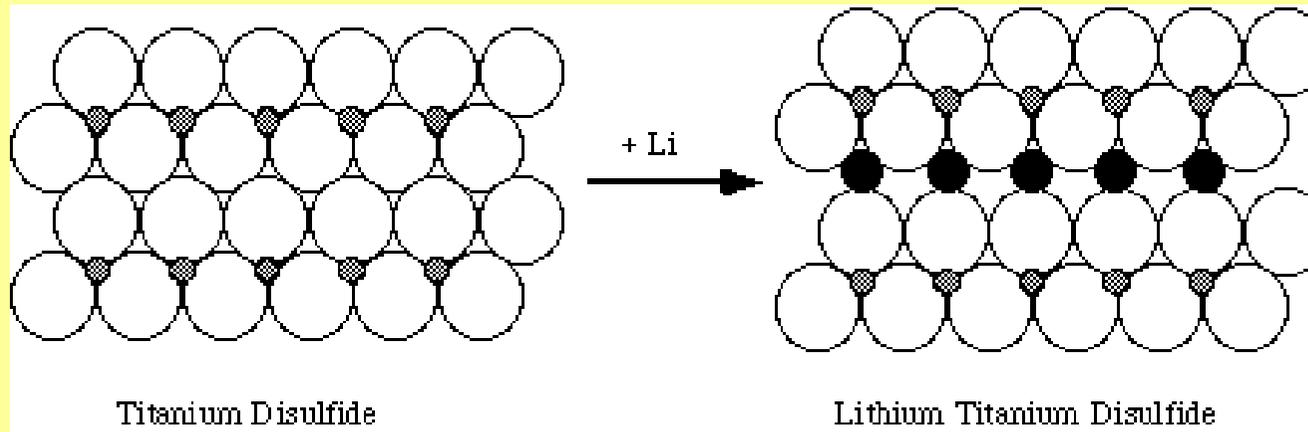


Li Intercalation

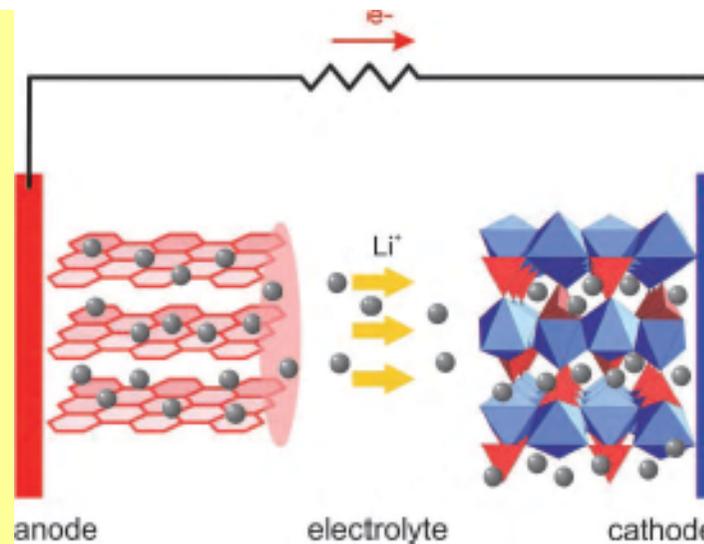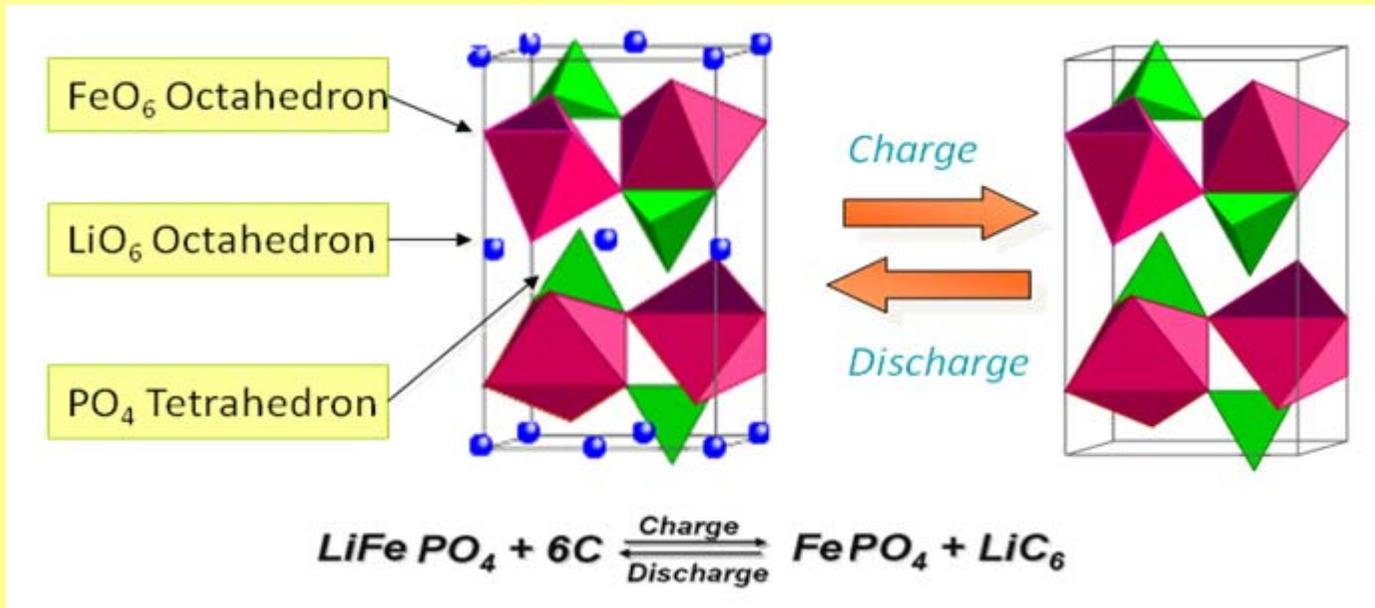

3D Intercalation Compounds

Cu_3N and Mn_3N crystallize in the (anti-) ReO_3 -type structure

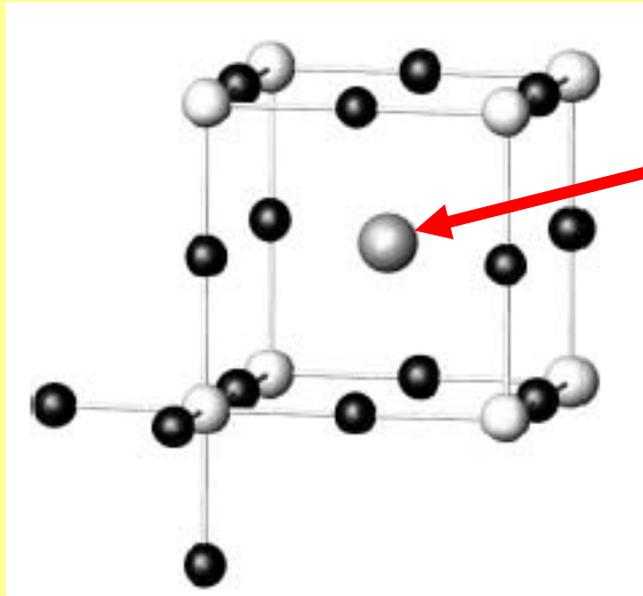

the large cuboctahedral void in the structure can be filled

By Pd to yield (anti-) perovskite-type PdCu_3N



By $M = \text{Ga}, \text{Ag}, \text{Cu}$ leading to MMn_3N

3D Intercalation Compounds

Tungsten trioxide structure

= WO_6 octahedra joined at their corners

= the perovskite structure of CaTiO_3 with all the calcium sites vacant

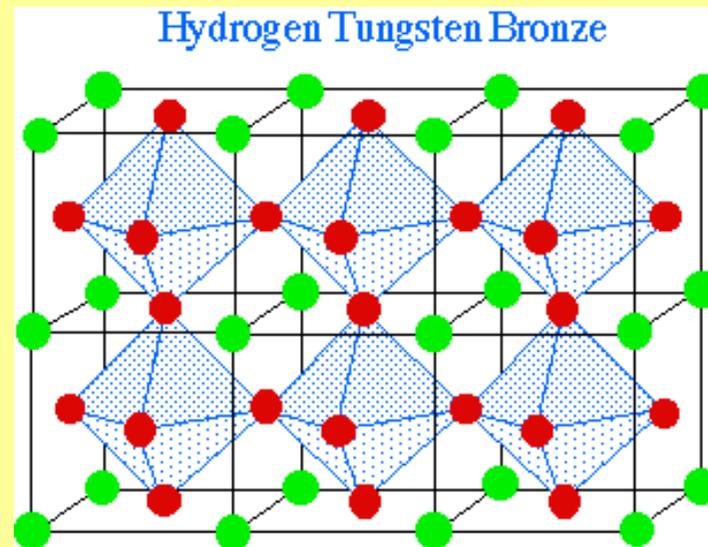

The color and conductivity changes are due to the intercalation of protons into the cavities in the WO_3 structure, and the donation of their electrons to the conduction band of the WO_3 matrix. The material behaves like a metal, with both its conductivity and color being derived from free electron behavior.

The coloration reaction used in electrochromic displays for sun glasses, rear view mirrors in cars

0D Intercalation Compounds

$C_{60} = \text{FCC}$

$K_3 C_{60}$

